UNITED STATES DEPARTMENT OF THE INTERIOR

GEOLOGICAL SURVEY

GEOLOGY, COAL RESOURCES, AND COAL QUALITY OF THE PRAIRIE DOG CREEK EMRIA STUDY AREA, ROSEBUD COUNTY, MONTANA

By

Laura N. Robinson, William C. Culbertson, and Ronald H. Affolter

Open-File Report 81-1136

1981

This report is preliminary and has not been edited or reviewed for conformity with U.S. Geological Survey standards.

Contents

Page

Abstract---------- iv

Introduction---------- 1

Previous investigations---------- 3

Structural setting---------- 3

Stratigraphy---------- 3

Coal geology---------- 7

Coal---------- 11

Origin---------- 11

Classification---------- 12

Rank of coal---------- 13

Type of coal---------- 17

Grade of coal---------- 18

Chemical analyses of coal in the Prairie Dog Creek study area---------- 19

Explanation of statistical terms used in summary tables---------- 37

Regional statistical comparison of composition of Prairie Dog Creek coal- 38

Composition of Prairie Dog Creek coals, by bed---------- 39

Estimation and classification of coal resources---------- 43

Tabulation of coal resources---------- 43

Characteristics used in resource evaluation---------- 45

Density---------- 45

Thickness of coal beds---------- 45

Depth of coal beds---------- 46

Resource categories according to degree of geologic assurance---- 47

Summary of coal resources---------- 48

References cited---------- 51

Illustrations

Page

Plate 1. Geologic map of the Prairie Dog Creek study area----------In pocket

2. Coal thickness, overburden thickness, and structure of the Wall coal bed----------In pocket

3. Thickness of Canyon coal bed, thickness of overburden, and thickness of interval between Canyon and Wall beds---In pocket

4. Thickness of Cook coal bed, thickness of overburden, and thickness of interval between Cook and Wall beds-----In pocket

Figure 1. Composite columnar section showing relations of Wall and Canyon beds to other coal beds in the Fort Union Formation---------- 5

2. Coal sections from drill holes---------- 8

3. Comparison on moist, mineral-matter-free basis of heat values and contents of moisture, volatile matter, and fixed carbon of coal of different ranks---------- 15

Tables

Table 1. Drill holes in and near the Prairie Dog Creek study area used in coal resource evaluation---------- 2

2. Generalized stratigraphic section of the northern Powder River Basin---------- 4

3. Classification of coals by rank---------- 16

4. Proximate and ultimate analyses, heat of combustion, forms-of-sulfur, and ash-fusion temperature determinations for 39 coal samples- 20

Page

5. Major- and minor-oxide and trace-element composition of the laboratory ash of 39 coal samples---------- 23
6. Contents of nine trace elements in 39 coal samples---------- 27
7. Major-, minor-, and trace-element composition of 39 coal samples---------- 28
8. Elements looked for but not detected in 39 coal samples------- 32
9. Arithmetic mean, observed range, geometric mean, and geometric deviation of proximate and ultimate analyses, heat of combustion, forms of sulfur, and ash-fusion temperatures of 39 coal samples---------- 33
10. Arithmetic mean, observed range, geometric mean, and geometric deviation of ash content and contents of nine major and minor oxides in the laboratory ash of 39 coal samples---------- 34
11. Arithmetic mean, observed range, geometric mean, and geometric deviation of 39 elements in 39 coal samples-------- 35
12. Average heat of combustion, moisture, ash, sulfur, content and apparent rank by coal bed, for 39 samples of coal---------- 41
13. Identified resources of potentially surface-minable coal in three beds---------- 49

Abstract

The 9800-acre (40-sq-km) Prairie Dog Creek EMRIA study area is located on the northwest flank of the northern Powder River Basin. Three major coal beds, in ascending order, the Wall, Cook, and Canyon, occur in gently southeast-dipping strata of the Tongue River Member of the Paleocene Fort Union Formation.

The Wall bed, reaching 62.5 feet (19.1 m) in thickness, contains 360 million short tons (327 million metric tons) of potentially surface-minable coal under less than 200 feet (61 m) of overburden. The Canyon and Cook beds contain resources of 35 million short tons (32 million metric tons) and 26 million short tons (24 million metric tons), respectively, under less than 200 feet (61 m) of overburden.

Additional resources from the three coal beds may be 300 million short tons (272 million metric tons) if 500 feet (152 m) of overburden is removed from the Wall bed.

Analyses of samples from core holes indicate that the apparent rank of the Wall coal bed is subbituminous B; the Canyon and Cook coal beds, subbituminous C. The three coal beds are well below the national average in ash and sulfur content.

Introduction

As a contribution to the study of the reclamation potential for surface mining, this report describes the geology and coal resources in a 9800-acre (40-sq-km) area located in the northern part of the Powder River Basin, T. 6 S., R. 41 E., Rosebud County, Mont. The Prairie Dog Creek study area was selected by the U.S. Bureau of Land Management for investigation as part of the Energy Minerals Rehabilitation Inventory and Analysis (EMRIA) Program. The area, including parts of the Birney SW and Taintor Desert 7.5-minute quadrangles, was mapped geologically in 1978 and 1979 by S. A. Volz (pl. 1).

Particular attention was focused on three coal beds in the Tongue River Member of the Fort Union Formation of Paleocene age: the Wall, Canyon, and Cook. Data on the coal beds were obtained from 18 drill holes in and near the study area, 10 of which were cored in 1978 and 1979 by the U.S. Bureau of Reclamation (table 1). Thirty-nine core samples of coal from six beds were analyzed to determine the composition and quality of the coal; the results of these analyses were statistically analyzed and are reported here by R. H. Affolter.

Table 1.--Drill holes in and near the Prairie Dog Creek study area used in coal resource evaluation

[USBR = U.S. Bureau of Reclamation; USGS = U.S. Geological Survey; MBMG = Montana Bureau of Mines and Geology. 1 ft = 0.305 m]

Map No.	Hole name and location	Surface elevation (in feet)	Cored interval (in feet)	Geophysical logs 1/
A	USBR DH 79-110 NE 1/4 sec. 5, T. 6 S., R. 41 E.	3795	0.5-174.0	
B	USBR DH 79-108 NE 1/4 sec. 6, T. 6 S., R. 41 E.	4025	.5-373.0	
C	MBMG SH 121 NE 1/4 sec. 12, T. 6 S., R. 40 E.	3865	---	2/
D	USBR DH 78-102 NW 1/4 sec. 7, T. 6 S., R. 41 E.	3910	.5-302.0	
E	USBR DH 78-105 SW 1/4 sec. 8, T. 6 S., R. 41 E.	3740	2.5-386.5	
F	USGS and MBMG US 76137 SW 1/4 sec. 8, T. 6 S., R. 41 E.	3720	---	Gamma Ray Density
G	USBR DH 79-106 SE 1/4 sec. 8, T. 6 S., R. 41 E.	3770	.5-220.0	
H	USGS water well, PDC 5 NW 1/4 sec. 16, T. 6 S., R. 41 E.	3705	---	Gamma Ray
I	USBR DH 79-107 SE 1/4 sec. 15, T. 6 S., R. 41 E.	3860	1.5-333.0	
J	MBMG SH 46 SW 1/4 sec. 16, T. 6 S., R. 41 E.	3601	40.0-89.0	2/
K	USBP DH 79-112 SE 1/4 sec. 18, T. 6 S., R. 41 E.	3805	1.0-214.5	
L	USBR DH 78-103 NW 1/4 sec. 21, T. 6 S., R. 41 E.	3620	.5-274.0	
M	MBMG SH 45 SW 1/4 sec. 21, T. 6 S., R. 41 E.	3586	57-104.0	2/
N	USBR DH 78-101 NE 1/4 sec. 29, T. 6 S., R. 41 E.	3830	2.0-399.0	
O	USGS water well, PDC 9 NE 1/4 sec. 29, T. 6 S., R. 41 E.	3835	---	Gamma Ray
P	USGS water well, PDC 11 NW 1/4 sec. 33, T. 6 S., R. 41 E.	3710	---	Gamma Ray
Q	USBR DH 79-111 SW 1/4 sec. 33, T. 6 S., R. 41 E.	3690	1.5-383.0	
R	USGS water well, PDC 13 SW 1/4 sec. 34, T. 6 S., R. 41 E.	3465	---	Gamma Ray

1/ Logs used for interpreting thickness of coal beds

2/ Data on these holes from Matson and others (1973) includes analyses of the Wall bed in SH-45 and SH-46.

Previous Investigations

The general geology of the Prairie Dog Creek study area was first mapped in the 1920's by Baker (1929) as part of a study of the northward extension of the Sheridan coal field. Later, Matson and others (1973) examined the area for strippable coal deposits. In 1978 and 1979, S. A. Volz (written communication, 1979) mapped the geology and coal deposits in the Birney SW and Taintor Desert 7.5-minute quadrangles and furnished the geologic map on plate 1.

Structural Setting

The Prairie Dog Creek study area lies on the gently dipping northwest flank of the northern Powder River Basin. In the study area the strata dip less than 1 degree to the southeast, and only locally are the strata affected by monoclinal folds and east-northeast-trending normal faults (pl. 2). Along the faults the strata are displaced a maximum of 100 feet (30 m), down to the south.

Stratigraphy

A generalized stratigraphic section of the Upper Cretaceous through Eocene rocks of the northern Powder River Basin is presented in table 2. The Prairie Dog Creek study area lies completely within the outcrop belt of the Tongue River Member of the Fort Union Formation (pl. 1). The principal coal-bearing part of the Tongue River Member in this area is about 700 feet (213 m) thick and locally contains 11 coal beds, of which 7 are more than 5 feet (1.5 m) thick. The non-coal rocks of this sequence consist of interbedded fine-grained to very fine grained sandstone, clayey siltstone, silty shale, and carbonaceous shale (see fig. 1).

The thicker coal beds have burned back from the outcrop in much of the study area. The resulting heat has baked and fused the overlying rocks into a brittle, resistant, red rock called clinker. Clinker beds are a prominent feature of the Prairie Dog Creek area.

Table 2.--Generalized stratigraphic section of the northern Powder River Basin

Age	Formation		Lithology
Eocene	Wasatch		Shale, sandstone, coal
Paleocene	Fort Union	Tongue River Member	Sandstone shale, siltstone, coal
		Lebo Shale Member	Dark shale
		Tullock Member	Shale, sandstone, minor coal
Late Cretaceous	Hell Creek		Sandstone, shale

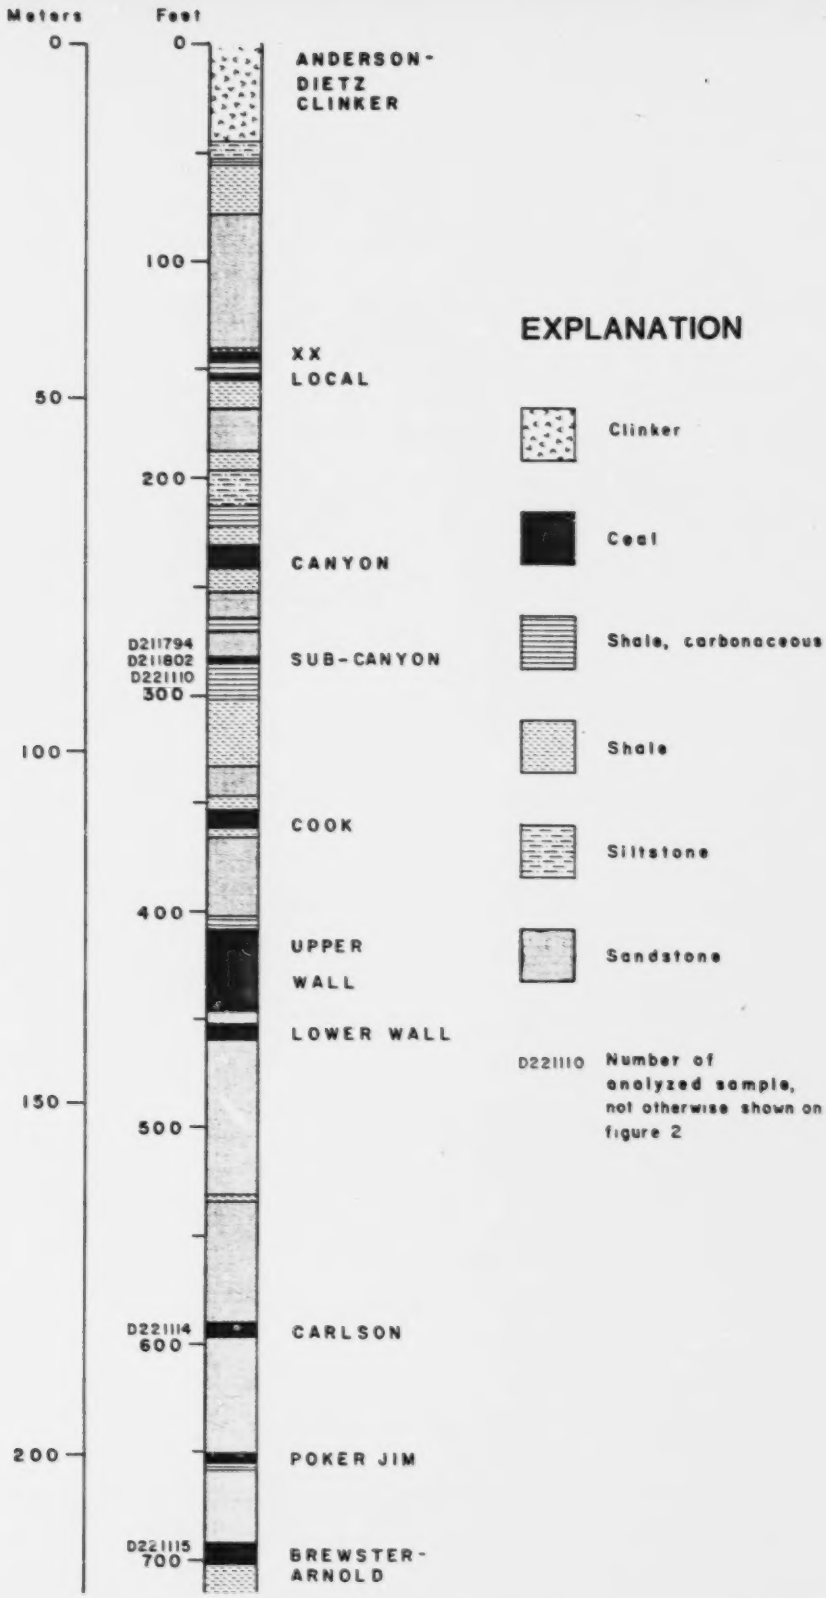

Figure 1 – Composite columnar section showing relations of Wall and Canyon beds to other coal beds in the Fort Union Formation. Section above Canyon from S. A. Volz (written communication, 1979)

Sediments in the Tongue River Member accumulated some 50 million years ago in rivers, flood plains, small lakes, and abundant swamps which migrated back and forth over a broad, flat alluvial plain.

The stream bottoms of Prairie Dog Creek and its tributaries are underlain by Quaternary alluvium which consists of unconsolidated sand, silt, clay, and gravel.

Coal Geology

The most important coal bed in this investigation is the Wall bed, which is 31.5 to 62.5 feet (9.6 to 19.1 m) thick in the study area. This coal bed generally thickens to the southwest, as shown by the isopach map on plate 2. The Wall bed is significantly thinner at locality Q than in nearby test holes, probably because of its location near a fault (pl. 2 and fig. 2).

Data from drill holes indicate that a parting exists in many places (fig. 2). In the southern part of the area the parting is 2 feet (0.6 m) or less in thickness, but it thickens to 7.8 feet (2.4 m) in the west-central part of area. Apparently it also thickens eastward because the Wall is represented on the eastern outcrop by two clinker beds as much as 60 feet (18.3 m) apart. Where the parting is more than 3 feet (1 m) thick, the upper and lower benches are here referred to as Upper and Lower Wall. The Lower Wall is 5.5 to 7.1 feet (1.7 to 2.2 m) thick, and the Upper Wall is 32.5 to 44.0 feet (9.9 to 13.4 m) thick.

The Wall coal bed is not exposed in the area. It burned back from its outcrop almost everywhere and formed clinker as much as 180 feet (55 m) thick in the southern part of the area.

The Cook bed is 2.6 to 8.6 feet (0.8 to 2.6 m) thick (fig. 2); it is 47 to 133 feet (14 to 41 m) above the Wall in six drill holes (pl. 4), but is missing entirely in holes at K, N, and O. Outcrop measurements range from 2.1 to 3.4 feet (0.6 to 1 m) (pl. 4). The geologic map indicates that the Cook is concealed or missing along most of its projected outcrop (pl. 1), but, for the purpose of calculating resources, an outcrop, or a limit of burned coal, was inferred from drill-hole and other data in the area (pl. 4).

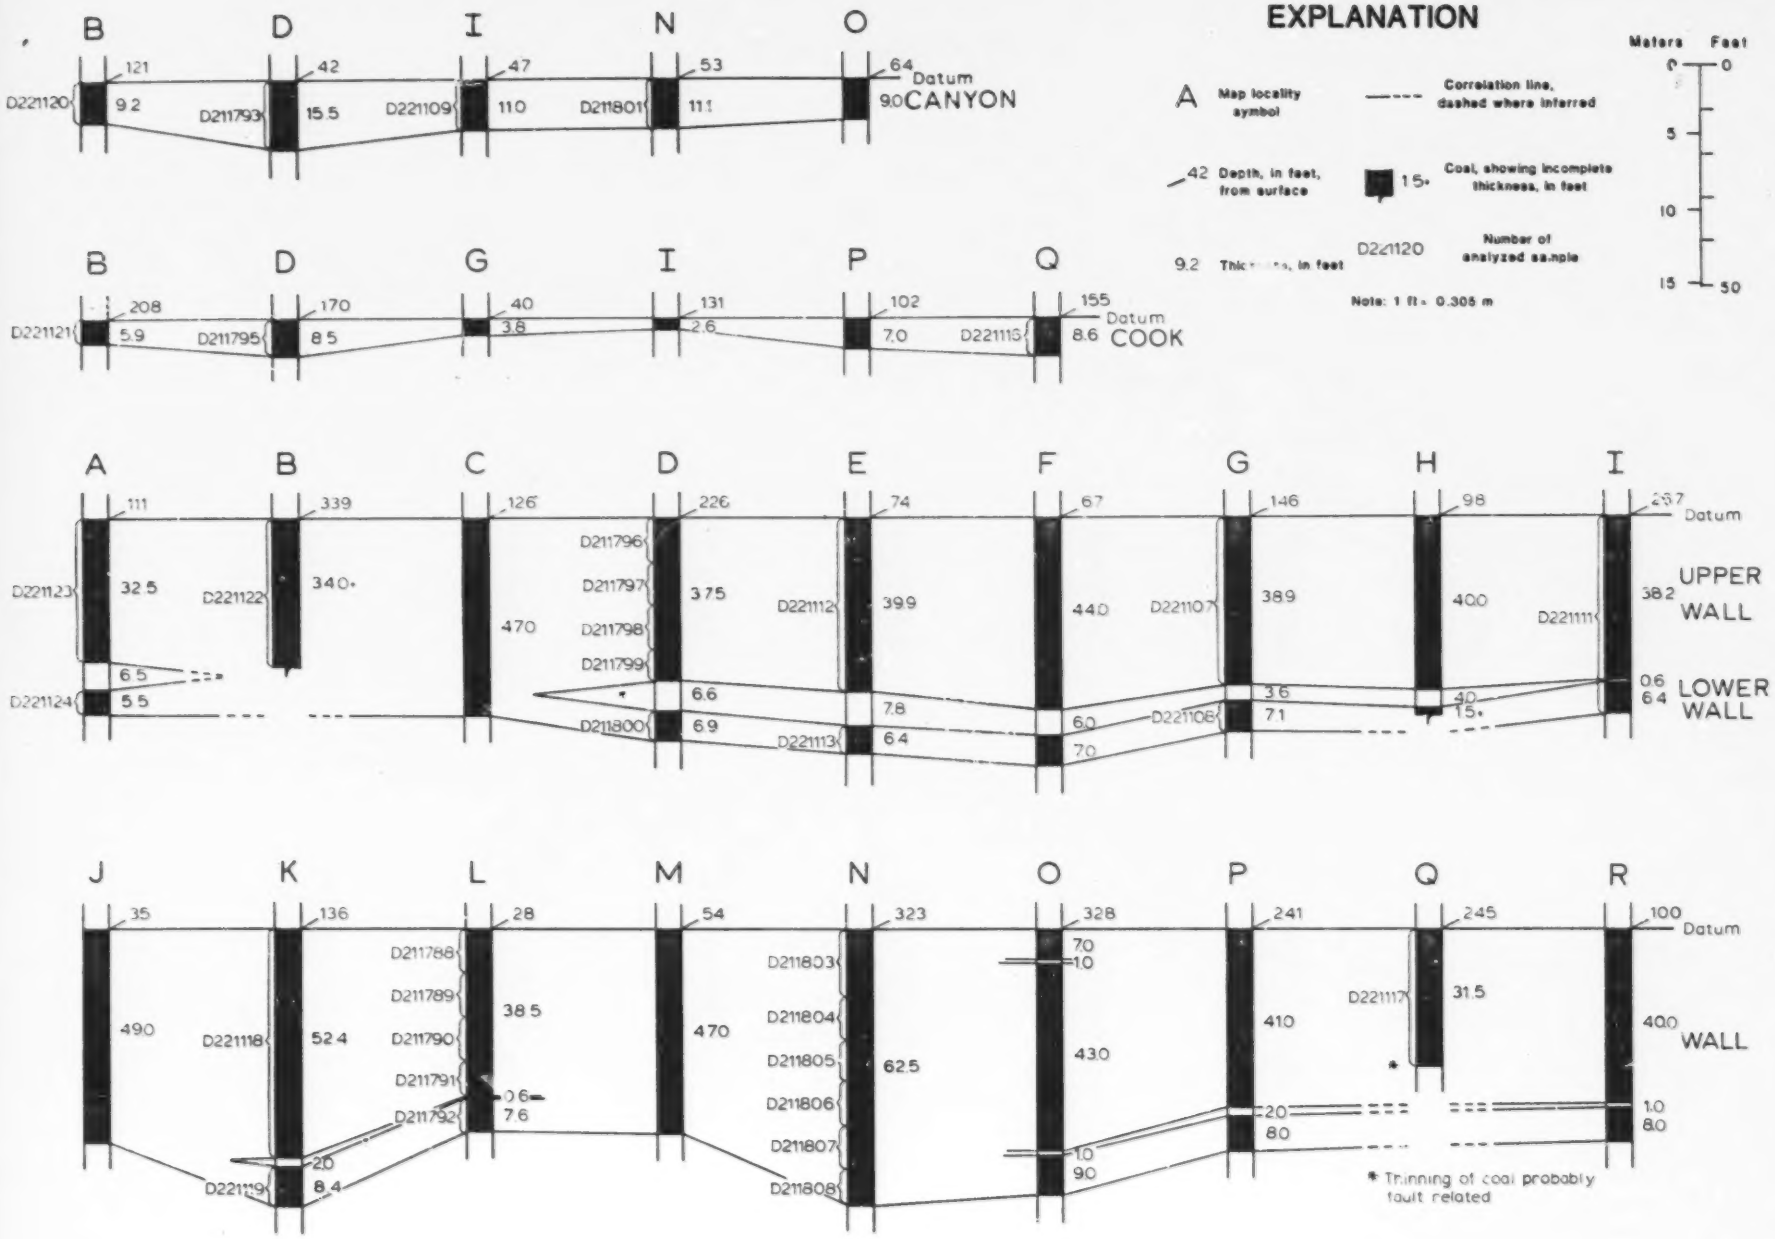

Figure 2 – Coal sections from drill holes in the Prairie Dog Creek study area

The sub-Canyon coal bed occurs between 120 and 220 feet (37-67 m) above the Wall in six drill holes. It is 1.0 foot thick (0.3 m) at hole B, 2.6 feet (0.8 m) at D, 6.0 feet (1.8 m) at I, 4.5 feet (1.4 m) at N, 4.0 feet (1.2 m) at O, and 3.5 feet (1.1 m) at P. The sub-Canyon was recognized on the outcrop only in the southern part of the study area (pl. 1).

The second most important coal bed in this area is the Canyon bed which is 160 to 260 feet (49-79 m) above the Wall (pl. 3). It is 9 to 15.5 feet (3 to 5 m) thick in five drill holes (fig. 2), thickening northwestward, but is as thin as 4.5 feet (1.4 m) on the outcrop. It is overlain by not more than 400 feet (120 m) of rock.

Three thin local coal beds lie within 40 to 160 feet (12 to 49 m) above the Canyon and are designated on the map (pl. 1) as L, XX, and X2. Sparse outcrop data indicate that they are 2 to 6 feet (0.6 to 18 m) thick. Remnants of the Anderson-Dietz bed underlie the high ridges in the area and are about 200 feet (61 m) above the Canyon. Much of it has burned, and no thickness data is available where it is not burned.

Beginning about 100 feet (30 m) below the Wall bed is a sequence of three or four coal beds (fig. 1). The uppermost bed, the Carlson, is 7.5 feet (2.3 m) thick and 130 feet (39.6 m) below the Wall in corehole E, but in corehole L it consists of four benches of coal totaling 5.2 (1.6 m) feet in an 8.1-foot (2.5-m) bed at 106 feet (32.3 m) below the Wall. The next bed, the Poker Jim, consists of interbedded coal and shale in both core holes. In corehole E it contains 4.5 feet (1.4 m) of coal in a 6.7-foot (2.0-m) bed that is 54 feet (16.5 m) below the Carlson and in corehole L it contains 4.5 feet (1.4 m) of coal in a 10.0-foot (3 m) bed. The thickest bed in this sequence is the Brewster-Arnold, which is 10.2 feet (3.1 m) thick at 237 feet (72.2 m) below the Wall in corehole E, the

only core hole that penetrated it. However, data from two oil and gas test holes (Culbertson, 1980) indicate that another bed, the Odell, lies 2 to 15 feet (0.6 to 4.6 m) below the Brewster-Arnold and is 6 to 7 feet (1.8 to .1 m) thick.

Coal

Origin

Coal has been defined as "a readily combustible rock containing more than 50 percent by weight and more than 70 percent by volume of carbonaceous material, formed from compaction or induration of variously altered plant remains similar to those of peaty deposits. Differences in the kinds of plant materials (type), in degree of metamorphism (rank), and range of impurity (grade), are characteristics of the varieties of coal" (Schopf, 1956). Coal deposits originated as a mixture of plant remains and inorganic mineral matter that accumulated in a manner similar to that in which modern-day peat deposits are formed. The peat then underwent a long, extremely complex process called "coalification," during which diverse physical and chemical changes occurred as the peat changed to coal, and the coal assumed the characteristics that differentiate it from other members of the coal series. The factors that affect the composition of coals have been summarized by Francis (1961, p. 2) as follows:

1) The mode of accumulation and burial of the plant debris forming the deposits.
2) The age of the deposits and their geographical distribution.
3) The structure of the coal-forming plant, particularly details of structure that affect chemical composition or resistance to decay.
4) The chemical composition of the coal-forming debris and its resistance to decay.
5) The nature and intensity of the plant-decaying processes.
6) The subsequent geological history of the residual products of decay of the plant debris forming the deposits.

The reader may refer to such standard works as Moore (1940), Lowry (1945, 1963), Tomkeieff, (1954), and Francis (1961) for further discussion of these factors.

Classification

Although coals can be classified in many ways (Tomkeieff, 1954, p. 9; Moore, 1940, p. 113; Francis, 1961, p. 361), classification by rank is the most commonly used system. Rank refers to the degree of metamorphism in the progressive series that begins with peat and ends with graphocite (Schopf, 1966). When sufficient megascopic and microscopic information is available classification by type of plant materials is commonly used as a descriptive adjunct to classification by rank. Classification by type and quantity of impurities (grade) or by coking qualities is often used.

Rank of coal

The designation of a coal within the metamorphic series, which begins with peat and ends with graphocite, is dependent upon the temperature and pressure to which the coal has been subjected and the length of time of subjection. Because coal is largely derived from plant material, it is mostly composed of carbon, hydrogen, and oxygen, along with smaller quantities of nitrogen, sulfur, and other elements. As coal undergoes progressive metamorphism, the increase in rank is indicated by changes in the proportions of the major coal constituents: a higher rank coal has more fixed carbon and less hydrogen and oxygen than the lower ranks.

The two standardized forms of coal analyses, the proximate analysis and the ultimate analysis, are described as follows (U.S. Bureau of Mines, 1965, p. 121-122):

> "The <u>proximate analysis</u> of coal involves the determination of four constituents: (1) water, called moisture; (2) mineral impurity, called ash, left when the coal is completely burned; (3) volatile matter, consisting of gases or vapors driven out when coal is heated to certain temperatures; and (4) fixed carbon, the solid or cakelike residue that burns at higher temperatures after volatile matter has been driven off. <u>Ultimate analysis</u> involves the determination of carbon and hydrogen as found in the gaseous products of combustion, the determination of sulfur, nitrogen, and ash in the materials as a whole, and the estimation of oxygen by difference."

Because most coals are burned to produce heat energy, the heating value of the coal is an important property. The heating value (calorific value) is commonly expressed in British thermal units (Btu) per pound: 1 Btu is the amount of heat required to raise the temperature of 1 pound of water $1^{\circ}F$ (1 Btu per pound = 0.5666 kilocalories per kilogram). Additional tests are sometimes made, particularly to determine forms of sulfur, ash-fusion temperatures, tar yield, caking, coking, and other properties that affect classification, utilization, or preparation of coal.

In histogram form, figure 3 compares the heating value, and the moisture, volatile-matter, and fixed-carbon contents of coals of different ranks.

Various schemes for classifying coals by rank have been proposed and used, but the one most commonly employed in the United States is the "Standard specifications for classification of coals by rank," adopted by the ASTM (American Society for Testing and Materials, 1977; table 1). It is reproduced here as table 3.

In the ASTM classification system, coals are divided into classes and groups according to either the mineral-matter-free fixed carbon or volatile matter content, or the moist-mineral-matter-free heating value, supplemented by determination of agglomerating (caking) characteristics (table 3). "Coals which in the volatile matter determination produce either an agglomerate button that will support a 500-g weight without pulverizing, or a button showing swelling or cell structure, shall be considered agglomerating from the standpoint of classification" (ASTM, 1977, p. 216).

Samples of coal must be obtained in accordance with standardized sampling procedures (Snyder, 1950; Schopf, 1960) in order to determine a standard rank, as pointed out by the ASTM (1977, p. 216). However, nonstandard samples may be used for comparative purposes through determinations designated as "apparent rank."

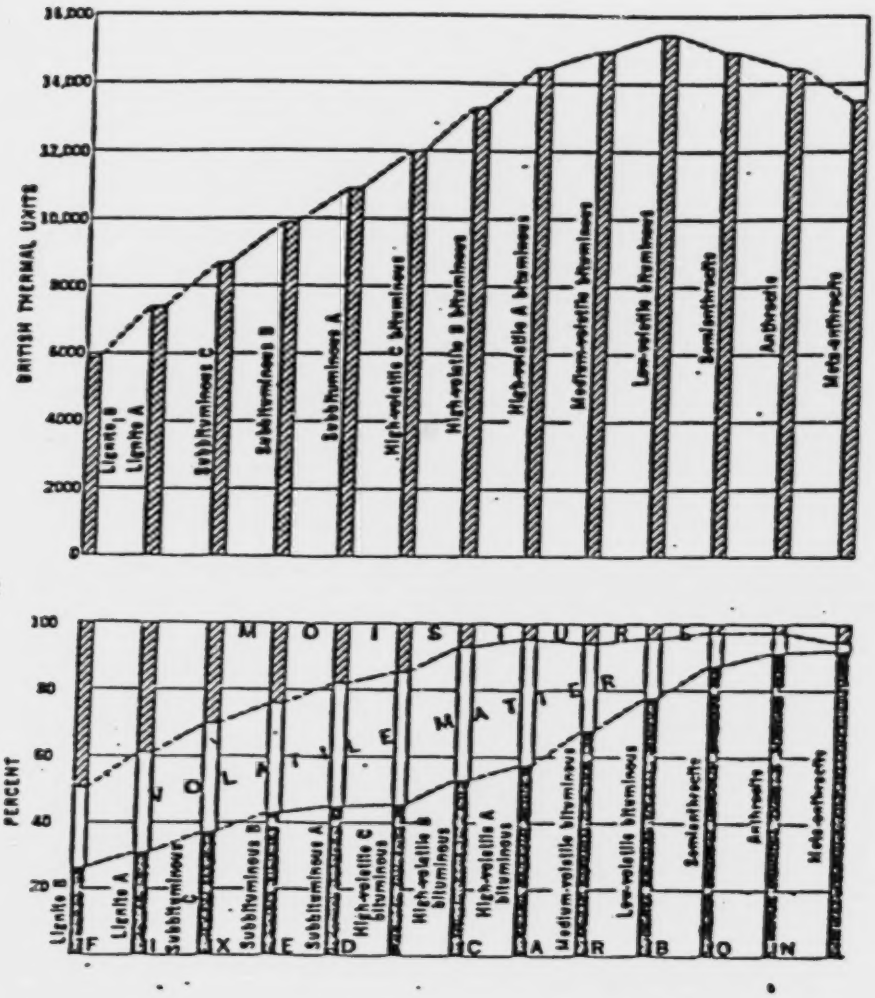

Figure 3.--Comparison on moist, mineral-matter-free basis of heat values and contents of moisture, volatile matter, and fixed carbon of coal of different ranks.

Table 3.--Classification of coals by rank[1]

[American Society for Testing and Materials Standard D388-66 (Reapproved 1972); 1 Btu equals 0.252 kilogram-calories]

Class	Group	Fixed Carbon Limits, percent (Dry, Mineral-Matter-Free Basis)		Volatile Matter Limits, percent (Dry, Mineral Matter-Free Basis)		Calorific Value Limits, Btu per pound (Moist,[2] Mineral-Matter-Free Basis)		Agglomerating Character
		Equal or Greater Than	Less Than	Greater Than	Equal or Less Than	Equal or Greater Than	Less Than	
I. Anthracite	1. Meta-anthracite	98	---	---	2	---	---	nonagglomerating
	2. Anthracite	92	98	2	8	---	---	
	3. Semianthracite[3]	86	92	8	14	---	---	
II. Bituminous	1. Low volatile bituminous coal	78	86	14	22	---	---	commonly agglomerating[5]
	2. Medium volatile bituminous coal	69	78	22	31	---	---	
	3. High volatile A bituminous coal	---	69	31	---	14 000[4]	---	
	4. High volatile B bituminous coal	---	---	---	---	13 000[4]	14 000	
	5. High volatile C bituminous coal	---	---	---	---	11 500	13 000	
						10 500	11 500	agglomerating
III. Subbituminous	1. Subbituminous A coal	---	---	---	---	10 500	11 500	nonagglomerating
	2. Subbituminous B coal	---	---	---	---	9 500	10 500	
	3. Subbituminous C coal	---	---	---	---	8 300	9 500	
IV. Lignitic	1. Lignite A	---	---	---	---	6 300	8 300	
	2. Lignite B					---	6 300	

[1]This classification does not include a few coals, principally nonbanded varieties, which have unusual physical and chemical properties and which come within the limits of fixed carbon or calorific value of the high-volatile bituminous and subbituminous ranks. All of these coals either contain less than 48 percent dry, mineral-matter-free fixed carbon or have more than 15,500 moist, mineral-matter-free British thermal units per pound.

[2]Moist refers to coal containing its natural inherent moisture but not including visible water on the surface of the coal.

[3]If agglomerating, classify in low-volatile group of the bituminous class.

[4]Coals having 69 percent or more fixed carbon on the dry, mineral-matter-free basis shall be classified according to fixed carbon, regardless of calorific value.

[5]It is recognized that there may be nonagglomerating varieties in these groups of the bituminous class, and there are notable exceptions in high volatile C bituminous group.

The apparent ranks of the coals at the Prairie Dog Creek study area are subbituminous C and B.

Type of coal

Classification of coals by type of plant materials present takes many forms, such as the "rational analysis" of Francis (1961) or the semicommercial "type" classification commonly used in the coal fields of the eastern United States (U.S. Bureau of Mines, 1965, p. 123). However, the majority of the type classifications are based on the same or similar gross distinctions in plant material to those used by Tomkeieff (1954, table II and p. 9), who divided the coals into three series: humic coals, humic-sapropelic coals, and sapropelic coals, according to the nature of the original plant materials. The humic coals are largely composed of the remains of the woody parts of plants, and the sapropelic coals are largely composed of the more resistant waxy, fatty, and resinous parts of plants, such as cell walls, spore-coatings, pollen, and resin particles. Some sapropelic coals are composed mainly of algal material. Most coals are classified in the humic series, with other coals being mixtures of humic and sapropelic elements and, therefore, classified in the humic-sapropelic series. The sapropelic series is quantitatively insignificant and, when found, is commonly regarded as an organic curiosity.

In common with most coals of the United States, the Prairie Dog Creek coals fall largely in the humic series.

Grade of coal

Classification of coal according to grade is based largely on the content of ash, sulfur, and other constituents that adversely affect utilization. Most detailed coal resource evaluations of the past did not categorize known coal resources by grade, but coals of the United States have been classified by sulfur content in a gross way (DeCarlo and others, 1966).

Compared to other U.S. coals (Swanson and others, 1976; Hatch and Swanson, 1977), coal from the Canyon, Cook, and Wall beds in the Prairie Dog Creek study area is characterized by relatively low ash, low sulfur, low heat of combustion, and high moisture content (table 4). The amounts of elements of environmental concern such as As, Be, Hg, Mo, Sb, and Se are low in the Prairie Dog Creek study area coal when compared to most other U.S. coals.

Chemical analyses of coal in the Prairie Dog Creek study area

Proximate and ultimate analysis,and heat-of-combustion, air-dried-loss, forms-of-sulfur and ash-fusion-temperature determinations on 39 samples from six coal beds (table 4) were provided by chemists from the Coal Analysis Section (John Puskas, Acting Chief), Department of Energy, Pittsburgh, P., whose contribution is gratefully acknowledged.

Analyses for ash content and 31 major and minor oxides and trace elements in the laboratory ash (table 5) and analyses of 9 trace elements in whole coal (table 6) for all 39 samples were provided by the U.S. Geological Survey, Denver. Analytical procedures used by the U.S. Geological Survey are described in Swanson and Huffman (1976).

We gratefully acknowledge the contribution of the team of chemical laboratory personnel in the U.S. Geological Survey under the direction of James L. Seeley: James W. Baker, Ardith J. Bartel, Joseph H. Christie, M. Coughlin, Barbara Keaten, Roy J. Knight, Sally Lasater, Fred E. Lichte, Jane Malcolm, Hugh T. Millard, Harriet G. Neiman, M. Schneider, Gaylord D. Shipley, Wenda Stang, Joseph E. Taggart, James A. Thomas, Robert B. Vaughn, and James S. Wahlberg.

Table 7 contains both the data listed in table 5 converted to a whole coal basis, and the whole-coal analyses that are listed in table 6. Twenty-three additional elements not listed in tables 5, 6, and 7 were looked for but not found in amounts greater than their lower limits of detection (table 8). Unweighted statistical summaries of the analytical data for 39 coal samples from the Prairie Dog Creek study area in tables 4, 5 and 6 are listed in tables 9, 10, and 11. For comparison, data summaries for coal samples from the Powder River region of Montana and Wyoming are included in tables 9, 10, and 11.

Table 4.--Proximate and ultimate analyses, heat-of-combustion, forms-of-sulfur, and ash-fusion-temperature determinations for 39 coal samples from Prairie Dog Creek study area, Rosebud County, Montana

[All analyses except heat of combustion and ash-fusion temperatures, in percent. For each sample number, the analyses are reported three ways: first, as received; second, moisture free; and third, moisture and ash free. All analyses by Coal Analysis Section, U.S. Department of Energy, Pittsburgh, Pa. Free-swelling-index not determined. L, less than value show. $F^{o} = (C^{o} \times 1.8) + 32$. Leaders (---) indicate no data. All samples are from the Fort Union Formation of Paleocene age. See plate 1 for locations and table 1 for data on drill holes]

Sample No.	Map locality	Coal bed	Depth interval in feet (meters)	Proximate analysis: Moisture	Volatile matter	Fixed carbon	Ash	Ultimate analysis: Hydrogen	Carbon	Nitrogen	Oxygen	Sulfur	Heat of combustion: Kcal/kg	Btu/lb	Air dried loss	Forms of sulfur: Sulfate	Pyritic	Organic	Ash-fusion temperature, C°: Initial deformation	Softening	Fluid
D221120	B	Canyon	121.3-130.5	28.2	27.5	39.7	4.6	6.2	50.3	1.0	37.4	0.4	4,750	8,550	20.7	0.01L	0.05	0.34	1,020	1,105	1,150
			(37.0-39.8)	---	38.3	55.3	6.4	4.3	70.2	1.4	17.2	.5	6,620	11,910	---	.01L	.07	.47			
				---	41.0	59.0	---	4.6	75.0	1.5	18.4	.6	7,060	12,710	---	.01L	.07	.51			
D211793	D	Canyon	42.5-58.0	30.6	27.3	38.9	3.2	6.7	49.4	1.0	39.4	.4	4,730	8,510	25.4	.01	.04	.33	1,290	1,350	1,395
			(13.0-17.7)	---	39.3	56.1	4.6	4.7	71.2	1.4	17.6	.5	6,820	12,280	---	.01	.05	.48			
				---	41.2	58.8	---	4.9	74.7	1.4	18.4	.6	7,150	12,870	---	.01	.06	.50			
D221109	I	Canyon	47.0-58.0	22.2	25.1	37.3	15.4	5.6	46.4	1.0	31.2	.5	4,360	7,850	16.4	.01	.13	.32	1,160	1,205	1,275
			(14.3-17.7)	---	32.3	48.0	19.7	4.0	59.7	1.2	14.8	.6	5,610	10,090	---	.01	.17	.41			
				---	40.3	59.7	---	5.0	74.4	1.5	18.4	.7	6,980	12,570	---	.01	.21	.51			
D211801	N	Canyon	52.7-63.8	29.5	29.1	38.1	3.3	6.4	50.1	1.1	38.6	.5	4,740	8,530	24.4	.01	.08	.41	1,130	1,180	1,225
			(16.1-19.5	---	41.3	54.0	4.7	4.5	71.1	1.6	17.4	.7	6,730	12,110	---	.01	.11	.58			
				---	43.4	56.6	---	4.7	74.6	1.6	18.3	.7	7,060	12,710	---	.01	.11	.61			
D211794	D	Sub Canyon	99.0-101.6	26.1	26.1	30.6	17.2	5.7	40.0	.8	33.6	2.7	3,880	6,990	20.1	.26	1.50	.92	1,065	1,115	1,160
			(30.2-31.0)	---	35.4	41.3	23.3	3.8	54.2	1.1	14.0	3.6	5,250	9,460	---	.36	2.03	1.24			
				---	46.1	53.9	---	4.9	70.7	1.5	18.3	4.7	6,850	12,330	---	.47	2.65	1.62			
D221110	I	Sub Canyon	79.0-85.0	19.3	27.0	37.0	16.7	5.3	46.0	.9	28.0	3.2	4,420	7,950	13.4	.17	1.91	1.08	1,050	1,110	1,150
			(24.1-25.9)	---	33.4	45.9	20.7	3.9	56.9	1.1	13.4	3.9	5,470	9,840	---	.22	2.36	1.34			
				---	42.1	57.9	---	4.9	71.8	1.4	17.0	4.9	6,900	12,420	---	.27	2.98	1.69			
D211802	N	Sub Canyon	91.0-95.3	27.8	29.1	36.4	6.7	6.4	47.6	.8	36.2	2.2	4,560	8,210	23.9	.14	.94	1.17	1,050	1,100	1,160
			(27.7-29.1)	---	40.3	50.4	9.3	4.6	66.0	1.2	15.9	3.1	6,320	11,380	---	.19	1.30	1.61			
				---	44.4	55.6	---	5.0	72.7	1.3	17.5	3.4	6,970	12,540	---	.21	1.43	1.78			
D221121	B	Cook	208.1-214.0	27.3	28.3	39.0	5.4	6.2	50.4	.9	36.7	.4	4,740	8,530	21.1	.01L	.03	.37	1,040	1,105	1,155
			(63.5-65.3)	---	38.9	53.7	7.4	4.3	69.4	1.3	17.1	.6	6,520	11,740	---	.01L	.04	.51			
				---	42.0	58.0	---	4.7	74.9	1.4	18.4	.6	7,040	12,670	---	.01L	.05	.55			
D211795	D	Cook	170.3-178.8	28.4	26.4	39.9	5.3	6.4	49.7	.9	37.4	.4	4,680	8,420	23.0	.02	.04	.38	1,125	1,180	1,230
			(51.9-54.5)	---	36.9	55.7	7.4	4.5	69.4	1.2	16.9	.6	6,540	11,760	---	.02	.05	.53			
				---	39.8	60.2	---	4.8	75.0	1.3	18.2	.7	7,060	12,710	---	.02	.06	.57			
D221116	Q	Cook	155.4-164.0	23.4	27.3	35.9	13.4	5.9	47.3	.9	31.4	1.0	4,540	8,180	17.2	.01	.27	.76	1,215	1,290	1,360
			(47.4-50.0)	---	35.6	46.9	17.5	5.3	61.8	1.2	13.9	1.4	5,930	10,680	---	.01	.36	1.00			
				---	43.1	56.9	---	5.2	74.9	1.5	16.8	1.7	7,750	12,950	---	.01	.43	1.21			
D221123	A	Upper Wall	111.0-143.5	25.0	30.1	40.3	4.6	6.3	52.7	.8	35.2	.3	4,990	8,990	19.8	.01	.06	.25	1,225	1,270	1,340
			(33.5-43.8)	---	40.2	53.6	6.2	4.8	70.3	1.0	17.3	.4	6,660	11,990	---	.01	.07	.33			
				---	42.8	57.2	---	5.1	74.9	1.1	18.5	.4	7,100	12,780	---	.01	.08	.35			
D221124	A	Lower Wall	150.0-155.5	21.6	29.9	41.7	6.8	6.0	53.9	.8	31.8	.7	5,140	9,250	16.7	.01	.17	.54	1,225	1,275	1,325
			(45.8-47.4)	---	38.2	53.2	8.6	4.6	68.7	1.0	16.1	.9	6,550	11,800	---	.01	.22	.68			
				---	41.8	58.2	---	5.1	75.2	1.1	17.6	1.0	7,180	12,920	---	.01	.24	.75			
D221122	B	Upper Wall	339.0-373.0	21.8	29.7	40.6	7.9	5.9	53.1	.8	31.9	.4	5,020	9,040	14.1	.01L	.09	.30	1,030	1,110	1,155
			(103.4-113.8)	---	38.0	51.8	10.2	4.4	67.9	1.0	16.0	.5	6,420	11,550	---	.01L	.12	.39			
				---	42.3	57.7	---	4.9	75.6	1.1	17.8	.6	7,140	12,860	---	.01L	.13	.43			
D211796	D	Upper Wall	226.0-236.0	26.6	27.8	37.9	7.7	6.1	49.1	1.0	35.6	.5	4,680	8,420	21.5	.01	.16	.37	1,070	1,115	1,175
			(68.9-72.0)	---	37.9	51.6	10.5	4.3	67.0	1.3	16.3	.7	6,370	11,470	---	.01	.21	.50			
				---	42.4	57.6	---	4.8	74.8	1.5	18.2	.8	7,120	12,810	---	.01	.24	.56			

Table 4.--Proximate and ultimate analyses, heat-of-combustion, forms-of-sulfur, and ash-fusion-temperature determinations for 39 coal samples from Prairie Dog Creek study area, Rosebud County, Montana--Continued

Sample No.	Map locality	Coal bed	Depth interval in feet (meters)	Proximate analysis				Ultimate analysis					Heat of combustion		Forms of sulfur			Ash-fusion temperature, C°		
				Moisture	Volatile matter	Fixed carbon	Ash	Hydrogen	Carbon	Nitrogen	Oxygen	Sulfur	Kcal/kg	Btu/lb	Air dried loss	Sulfate	Pyritic	Organic	Initial deformation	Softening	Fluid
D211797	D	Upper Wall	236.0-246.0 (72.0-75.0)	26.6	30.4	37.8	5.2	6.4	50.7	0.7	36.7	0.2	4,890	8,800	21.4	0.01	0.03	0.19	1,070	1,150	1,190
				---	41.4	51.5	7.1	4.6	69.1	1.0	17.8	.3	6,650	11,980	---	.01	.04	.26			
				---	44.6	55.4	---	5.0	74.4	1.1	19.1	.3	7,170	12,900	---	.01	.05	.28			
D211798	D	Upper Wall	246.0-256.0 (75.0-78.1)	27.0	31.5	37.9	3.6	6.5	50.9	.7	38.2	.2	5,000	9,000	22.2	.01	.04	.16	1,045	1,090	1,140
				---	43.1	52.0	4.9	4.8	69.7	1.0	19.4	.3	6,840	12,320	---	.01	.05	.22			
				---	45.3	54.7	---	5.0	73.3	1.0	20.4	.3	7,200	12,960	---	.01	.06	.23			
D211799	D	Upper Wall	256.0-263.5 (78.1-80.4)	28.4	29.3	38.7	3.6	6.5	50.4	0.7	38.4	.4	4,880	8,780	23.3	.01	.06	.29	1,120	1,170	1,220
				---	40.9	54.0	5.1	4.6	70.3	1.0	18.4	.5	6,810	12,260	---	.01	.09	.40			
				---	43.1	56.9	---	4.9	74.1	1.1	19.4	.5	7,180	12,920	---	.01	.09	.43			
D211800	D	Lower Wall	270.1-277.0 (82.4-84.5)	28.0	29.4	38.7	3.9	6.4	50.9	.8	37.5	.5	4,900	8,830	22.2	.01	.09	.45	1,095	1,140	1,175
				---	40.8	53 7	5.5	4.6	70.8	1.1	17.5	.8	6,810	12,260	---	.01	.13	.62			
				---	43.1	56.9	---	6.8	74.8	1.1	18.5	.8	7,200	12,970	---	.01	.14	.65			
D221112	E	Upper Wall	74.3-114.2 (22.7-34.8)	25.2	29.5	41.1	4.2	6.3	53.3	.8	34.8	.4	5,070	9,120	17.7	.01	.13	.29	1,140	1,170	1,240
				---	39.4	54.9	5.7	4.7	71.3	1.1	16.6	.6	6,780	12,200	---	.01	.18	.39			
				---	41.8	58.2	---	5.0	75.6	1.2	17.6	.6	7,180	12,930	---	.01	.19	.41			
D221113	E	Lower Wall	122.0-128.4 (37.2-39.2)	20.3	30.5	45.5	3.7	6.1	57.1	1.0	31.6	.5	5,440	9,790	15.4	.01	.09	.41	1,145	1,190	1,250
				---	38.3	57.1	4.6	4.9	71.7	1.2	17.1	.6	6,820	12,280	---	.01	.12	.51			
				---	40.1	59.9	---	5.1	75.1	1.3	17.9	.7	7,150	12,870	---	.01	.12	.54			
D221107	G	Upper Wall	146.1-185.0 (44.6-56.4)	20.7	30.5	43.6	5.2	6.2	55.9	.9	31.5	.3	5,330	9,600	16.2	.01	.08	.23	1,045	1,095	1,155
				---	38.5	54.9	6.6	4.9	70.4	1.1	16.6	.4	6,720	12,090	---	.01	.10	.29			
				---	41.2	58.8	---	5.3	75.4	1.2	17.8	.4	7,190	12,950	---	.01	.10	.32			
D221108	G	Lower Wall	188.6-195.7 (57.5-59.7)	22.0	30.5	42.1	5.4	6.2	54.7	.8	32.2	.7	5,180	9,330	15.9	.01	.17	.52	1,010	1,060	1,115
				---	39.0	54.1	6.9	4.8	70.1	1.0	16.2	.9	6,640	11,960	---	.01	.22	.67			
				---	42.0	58.0	---	5.1	75.4	1.1	17.5	1.0	7,140	12,850	---	.01	.23	.72			
D221111	I	Wall	267.0-312.2 (81.4-95.2)	20.6	29.3	43.4	6.7	6.0	54.7	.9	31.2	.4	5,230	9,420	15.9	.01	.09	.34	1,080	1,155	1,220
				---	36.9	54.7	8.4	4.7	68.9	1.1	16.2	.6	6,590	11,870	---	.01	.12	.43			
				---	40.3	59.7	---	5.2	75.3	1.2	17.7	.6	7,200	12,960	---	.01	.13	.47			
D221118	K	Wall	135.6-188.4 (41.4-57.5)	24.6	30.0	40.2	5.2	6.2	53.1	.8	34.3	.4	5,040	9,070	17.5	.01	.08	.32	1,105	1,145	1,190
				---	39.8	53.3	6.9	4.6	70.4	1.0	16.5	.5	6,680	12,030	---	.01	.11	.42			
				---	42.8	57.2	---	5.0	75.6	1.1	17.7	.6	7,180	12,920	---	.01	.12	.45			
D221119	K	Wall	190.4-198.8 (58.1-60.6)	26.5	28.7	41.1	3.7	6.5	52.4	.8	35.8	.7	5,020	9,040	22.4	.01	.19	.52	1,020	1,070	1,115
				---	39.1	55.9	5.0	4.9	71.4	1.1	16.7	1.0	6,830	12,300	---	.01	.26	.71			
				---	41.1	58.9	---	5.1	75.1	1.1	17.5	1.0	7,190	12,950	---	.01	.28	.75			
D211788	L	Wall	28.0-38.0 (8.5-11.6)	26.8	29.1	38.9	5.2	6.4	51.5	.8	35.6	.5	4,910	8,830	20.2	.01	.10	.42	1,020	1,070	1,130
				---	39.8	53.0	7.2	4.7	70.4	1.1	16.0	.7	6,700	12,070	---	.01	.13	.57			
				---	42.8	57.2	---	5.0	75.8	1.2	17.2	.8	7,220	12,990	---	.01	.14	.61			
D211789	L	Wall	38.0-48.0 (11.6-14.6)	27.0	29.7	39.7	3.6	6.6	52.3	.7	36.4	.3	4,980	8,970	21.5	.05	.05	.15	1,200	1,245	1,295
				---	40.7	54.3	5.0	5.0	71.6	1.0	17.0	.3	6,830	12,290	---	.08	.06	.20			
				---	42.9	57.1	---	5.3	75.4	1.0	17.9	.4	7,180	12,930	---	.08	.07	.21			
D211790	L	Wall	48.0-58.0 (14.6-17.7	27.6	32.0	37.4	3.0	6.6	52.4	.7	37.1	.2	4,970	8,950	21.6	.01	.02	.17	1,290	1,325	1,365
				---	44.1	51.7	4.2	4.9	72.3	1.0	17.4	.3	6,860	12,350	---	.01	.03	.23			
				---	46.1	53.9	---	5.1	73.4	1.0	18.1	.3	7,160	12,890	---	.01	.03	.24			
D211791	L	Wall	58.0-66.5 (17.7-20.3)	27.8	28.1	39.9	4.2	6.5	51.0	.7	37.0	.5	4,870	8,760	23.2	.01	.08	.38	1,125	1,170	1,220
				---	38.9	55.2	5.9	4.8	70.7	1.0	16.9	.7	6,740	12,140	---	.01	.12	.53			
				---	41.3	58.7	---	5.1	75.1	1.1	18.0	.7	7,170	12,900	---	.01	.12	.57			

Table 4.--Proximate and ultimate analyses, heat-of-combustion, forms-of-sulfur, and ash-fusion-temperature determinations for 39 coal samples from Prairie Dog Creek study area, Rosebud County, Montana--Continued

Sample No.	Map locality	Coal bed	Depth interval in feet (meters)	Proximate analysis				Ultimate analysis					Heat of combustion			Forms of sulfur			Ash-fusion temperature, C°		
				Moisture	Volatile matter	Fixed carbon	Ash	Hydrogen	Carbon	Nitrogen	Oxygen	Sulfur	Kcal/kg	Btu/lb	Air dried loss	Sulfate	Pyritic	Organic	Initial deformation	Softening	Fluid
D211792	L	Wall	67.1-74.7	28.9	28.3	39.6	3.2	6.7	51.3	0.8	37.6	0.5	4,900	8,820	21.3	0.02	0.07	0.37	1,110	1,160	1,210
			(20.5-22.8)	---	39.8	55.7	4.5	4.9	72.1	1.1	16.7	.6	6,890	12,400	---	.02	.10	.52			
				---	41.7	58.3	---	5.1	75.5	1.2	17.5	.7	7,210	12,980	---	.02	.10	.55			
D211803	N	Wall	323.0-338.0	25.4	28.8	39.1	6.7	6.3	50.9	.8	34.6	.7	4,850	8,730	20.5	.01	.17	.55	1,170	1,240	1,280
			(98.5-103.1)	---	38.6	52.4	9.0	4.6	68.2	1.0	16.1	1.0	6,490	11,690	---	.01	.22	.73			
				---	42.4	57.6	---	5.1	75.0	1.1	17.7	1.1	7,140	12,850	---	.01	.25	.81			
D211804	N	Wall	338.0-348.0	26.9	28.1	41.5	3.5	6.5	52.2	.7	36.8	.2	4,980	8,970	21.1	.01	.06	.19	1,260	1,295	1,325
			(103.1-106.1)	---	38.4	56.8	4.8	4.8	71.3	1.0	17.7	.3	6,810	12,260	---	.01	.08	.25			
				---	40.3	59.7	---	5.1	75.0	1.0	18.6	.4	7,130	12,890	---	.01	.08	.27			
D211805	N	Wall	348.0-358.0	25.9	31.5	39.4	3.2	6.5	53.1	.7	36.2	.2	5,120	9,220	20.3	.01	.04	.19	1,265	1,310	1,355
			(106.1-109.2)	---	42.4	53.2	4.4	4.9	71.6	1.0	17.8	.3	6,900	12,430	---	.01	.05	.26			
				---	44.4	55.6	---	5.1	74.9	1.0	18.6	.3	7,220	13,000	---	.01	.06	.27			
D211806	N	Wall	358.0-368.0	27.0	29.1	41.1	2.8	6.7	52.8	.8	36.7	.2	5,070	9,130	21.3	.02	.03	.17	1,280	1,330	1,370
			(109.2-112.2)	---	39.9	56.2	3.9	5.0	72.3	1.1	17.3	.3	6,950	12,520	---	.02	.04	.23			
				---	41.5	58.5	---	5.2	75.3	1.2	18.1	.3	7,240	13,030	---	.02	.04	.24			
D211807	N	Wall	368.0-378.0	26.5	29.4	37.9	6.2	6.2	50.4	.8	35.9	.4	4,850	8,740	21.8	.01	.09	.34	1,140	1,205	1,245
			(112.2-115.3)	---	40.0	51.6	8.4	4.5	68.5	1.1	16.9	.6	6,600	11,880	---	.01	.13	.46			
				---	43.7	56.3	---	4.9	74.8	1.2	18.4	.7	7,210	12,970	---	.01	.14	.50			
D211808	N	Wall	378.0-385.4	24.4	29.5	38.5	7.6	6.1	50.5	.9	34.2	.7	4,890	8,810	19.3	.01	.15	.57	1,110	1,160	1,205
			(115.3-117.3)	---	39.0	50.9	10.1	4.5	66.7	1.2	16.6	1.0	6,470	11,640	---	.01	.19	.75			
				---	43.4	56.6	---	5.0	74.2	1.3	18.4	1.1	7,190	12,950	---	.01	.21	.84			
D221117	Q	Wall	244.7-276.2	21.1	31.4	42.6	4.8	6.0	56.3	.9	31.3	.7	5,400	9,720	14.1	.01	.17	.51	1,040	1,100	1,145
			(74.6-84.2)	---	39.9	54.0	6.1	4.7	71.5	1.2	15.7	.9	6,850	12,340	---	.01	.22	.65			
				---	42.5	57.5	---	5.0	76.1	1.3	16.7	.9	7,300	13,140	---	.01	.23	.69			
D221114	E	Carlson	259.5-267.0	16.6	26.1	33.6	23.7	5.1	44.3	.9	24.9	1.2	4,220	7,600	11.7	.01	.34	.81	1,055	1,105	1,145
			(79.1-81.4)	---	31.3	40.3	28.4	3.9	53.1	1.1	12.2	1.4	5,060	9,110	---	.01	.40	.97			
				---	43.7	56.3	---	5.4	74.2	1.5	17.0	1.9	7,070	12,730	---	.01	.56	1.30			
D221115	E	Brewster-Arnold	365.8-376.0	24.4	28.1	39.7	7.8	6.1	51.1	1.0	33.4	.7	4,870	8,760	18.3	.01	.25	.40	1,080	1,130	1,180
			(111.6-114.7)	---	37.1	52.6	10.3	4.5	67.6	1.3	15.5	.9	6,440	11,590	---	.01	.32	.53			
				---	41.4	58.6	---	5.0	75.3	1.4	17.3	1.0	7,180	12,920	---	.01	.36	.59			

Table 5.--Major- and minor-oxide and trace-element composition of the laboratory ash of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[Values in percent or parts per million. Coal ashed at 525° C. L, less than the value shown; N, not detected; B, not determined. S after element title indicates determinations by semiquantitative emission spectrography. The spectrographic results are to be identified with geometric brackets whose boundaries are part of the ascending series 0.12, 0.18, 0.26, 0.38, 0.56, 0.83, 1.2, etc., but reported as midpoints of the brackets 0.1, 0.15, 0.2, 0.3, 0.5, 0.7, 1.0, etc. Precision of the spectrographic data is plus-or-minus one bracket at 68-percent or plus-or-minus two brackets at 95-percent confidence level]

Sample number	Ash (percent)	SiO2 (percent)	Al2O3 (percent)	CaO (percent)	MgO (percent)	Na2O (percent)	K2O (percent)	Fe2O3 (percent)	TiO2 (percent)	P2O5 (percent)	Sample number
D221120	5.2	26	9.1	15	5.97	10.4	0.56	5.3	0.47	1.2	D221120
D211793	4.3	17	10	20	11.4	.90	.40	6.6	.37	.23L	D211793
D221109	17.3	58	16	3.8	6.30	1.02	3.2	4.4	.55	.060L	D221109
D211801	4.9	24	10	15	6.30	8.30	.91	5.4	.43	.41	D211801
D211794	26.7	45	19	3.1	1.66	2.20	1.4	12	.62	.71	D211794
D221110	18.3	43	16	2.8	3.81	.66	1.6	19	.57	.11	D221110
D211802	9.8	24	10	6.9	3.98	2.50	.86	24	.37	.31	D211802
D221121	5.9	24	16	14	3.98	10.4	.12	3.0	.45	4.6	D221121
D211795	7.3	32	16	13	1.54	5.00	.23	2.9	.65	1.8	D211795
D221116	13.1	62	9.6	4.6	2.16	.66	.47	4.4	.70	.99	D221116
D221123	5.1	30	15	17	7.13	3.37	.46	4.7	.57	.39	D221123
D221124	7.2	39	12	11	4.31	4.04	.22	5.6	1.1	.56	D221124
D221122	8.8	45	15	8.4	2.32	6.47	1.1	4.9	.78	.45	D221122
D211796	10.6	39	16	8.5	2.16	6.40	.77	6.3	.58	.66	D211796
D211797	7.1	41	12	12	2.82	9.80	.12	3.4	1.2	.56	D211797
D211798	5.4	28	11	14	3.48	11.3	.25	5.3	.55	.37	D211798
D211799	5.1	21	11	14	3.48	11.6	.29	5.7	.50	.20	D211799
D211800	5.4	20	9.6	13	2.98	10.6	.25	7.4	.47	.19L	D211800
D221112	4.7	26	13	14	9.78	1.48	.24	7.2	.55	.21	D221112
D221113	4.2	19	12	17	8.46	1.35	.40	6.7	.45	.24L	D221113
D221107	5.7	32	13	13	2.49	9.84	.30	4.9	.73	.35	D221107
D221108	6.2	36	11	9.4	.02L	8.22	.22	7.2	.73	.16L	D221108
D221111	7.7	43	14	9.0	1.99	6.61	1.1	3.7	.82	.26	D221111
D221118	5.6	30	13	15	4.15	2.97	.35	8.2	.65	.36	D221118
D221119	4.2	15	8.0	12	2.82	12.1	.23	8.7	.37	.24	D221119
D211788	6.9	30	15	15	4.97	1.80	.20	5.4	.55	1.5	D211788
D211789	4.9	26	13	21	6.63	2.70	.20	5.0	.85	.41	D211789
D211790	4.4	24	11	22	6.73	3.10	.12	4.6	.60	.23	D211790
D211791	6.2	26	21	14	4.64	2.40	.23	6.0	.50	.97	D211791
D211792	4.5	20	9.5	17	4.48	7.28	.30	5.3	.47	1.1	D211792
D211803	8.6	36	16	11	4.97	.98	.37	6.0	.67	.58	D211803
D211804	4.5	24	13	21	9.45	2.20	.12	3.7	.82	.22L	D211804
D211805	4.4	24	15	21	8.95	3.00	.24	3.9	.78	.23L	D211805
D211806	4.1	24	11	21	8.79	3.60	.24	3.9	.62	.24L	D211806
D211807	7.3	36	16	11	5.14	2.70	1.2	4.2	.60	1.2	D211807
D211808	8.4	43	14	8.5	3.32	4.50	1.6	5.7	.62	.12L	D211808
D221117	5.4	28	13	12	1.29	9.30	.26	5.9	.57	.93	D221117
D221114	25.7	58	18	2.8	5.64	2.29	3.5	3.0	.62	.080	D221114
D221115	8.5	39	19	7.4	1.11	4.99	.77	6.6	.89	.47	D221115

Table 5.--Major- and minor-oxide and trace-element composition of the laboratory ash of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--continued

Sample number	B-S (ppm)	Ba-S (ppm)	Be-S (ppm)	Cd (ppm)	Ce-S (ppm)	Cu (ppm)	Ga-S (ppm)	Ge-S (ppm)	La-S (ppm)	Li (ppm)	Sample number
D221120	700	3,000	3	1.0L	500L	84	15	3	30	31	D221120
D211793	1,500	5,000	3	5.0	N	84	50	N	N	26	D211793
D221109	300	1,500	5	1.0L	500L	52	20	7	50	51	D221109
D211801	2,000	10,000	20	4.0	N	88	50	N	N	41	D211801
D211794	200	5,000	10	7.0	N	206	50	20	100L	94	D211794
D221110	300	2,000	10	1.0	500L	233	20	7	70	103	D221110
D211802	700	7,000	20	1.0	N	106	50	N	100L	42	D211802
D221121	700	3,000	7	1.0L	100	75	20	5	70	43	D221121
D211795	1,000	7,000	10	4.0	N	48	50	N	N	38	D211795
D221116	500	2,000	7	1.0	150	84	20	15	70	1	D221116
D221123	700	5,000	2	1.0L	500L	100	20	5	50	61	D221123
D221124	500	5,000	10	1.0L	500L	121	10	5	50	52	D221124
D221122	200	3,000	2	1.0L	500L	100	20	5	50	64	D221122
D211796	500	7,000	3L	5.0	N	89	30	N	100L	87	D211796
D211797	700	15,000	N	10.0	N	109	30	N	N	69	D211797
D211798	1,000	15,000	N	9.0	N	83	30	N	N	47	D211798
D211799	1,000	15,000	5	1.0	N	91	30	N	100L	54	D211799
D211800	1,500	7,000	20	1.0	N	87	50	N	N	36	D211800
D221112	700	5,000	3	1.0L	500L	100	20	5	50	40	D221112
D221113	1,000	7,000	15	1.0L	500L	78	20	2	50	19	D221113
D221107	500	5,000	3	1.0L	500L	82	15	3	50	55	D221107
D221108	700	1,500	10	1.0L	500L	75	15	3	30	40	D221108
D221111	500	3,000	3	1.0L	500L	91	15	3	30	57	D221111
D221118	700	3,000	2	1.0L	500L	93	15	3	50	65	D221118
D221119	700	5,000	10	1.0L	100	97	20	3	30	43	D221119
D211788	700	7,000	3	6.0	N	98	50	N	N	94	D211788
D211789	1,000	7,000	N	32.0	N	131	30	N	N	49	D211789
D211790	1,500	10,000	N	5.0	N	76	30	N	N	24	D211790
D211791	1,000	7,000	5	8.0	N	83	50	N	100L	131	D211791
D211792	1,500	7,000	10	11.0	N	79	30	N	N	37	D211792
D211803	700	7,000	5	2.0	N	113	50	70	100L	102	D211803
D211804	1,500	15,000	N	1.0L	N	105	30	N	N	55	D211804
D211805	1,500	15,000	N	2.0	N	112	30	N	N	55	D211805
D211806	1,500	15,000	N	1.0	N	86	30	N	N	33	D211806
D211807	1,000	7,000	N	1.0	N	92	30	N	N	62	D211807
D211808	1,000	7,000	20	2.0	N	94	70	N	N	40	D211808
D221117	700	3,000	5	1.0L	500L	98	20	15	50	56	D221117
D221114	200	2,000	10	1.0	500L	64	150	20	50	58	D221114
D221115	500	5,000	10	4.0	500L	87	30	7	50	93	D221115

Table 5.--Major- and minor-oxide and trace-element composition of the laboratory ash of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--continued

Sample number	Mn (ppm)	Mo-S (ppm)	Nb-S (ppm)	Ni-S (ppm)	Pb (ppm)	Sc-S (ppm)	Sr-S (ppm)	V-S (ppm)	Y-S (ppm)	Yb-S (ppm)	Sample number
D2 21120	366	15	15	20	99	7	3,000	70	20	1.5	D2 21120
D2 11793	437	70	N	50	155	20	3,000	150	70	5	D2 11793
D2 21109	204	5	20	50	25L	15	700	100	30	3	D2 21109
D2 11801	406	20	N	50	111	30	5,000	150	70	7	D2 11801
D2 11794	144	50	N	200	56	30	2,000	500	100	10	D2 11794
D2 21110	125	20	20	70	40	20	700	200	70	5	D2 21110
D2 11802	297	70	N	200	54	50	2,000	500	150	15	D2 11802
D2 21121	287	5	20	50	37	10	10L	15L	30	2	D2 21121
D2 11795	146	15	N	30	51	20	7,000	150	100	7	D2 11795
D2 21116	95	10	30	30	25L	15	1,500	100	50	5	D2 21116
D2 21123	249	7	20	30	47	10	10L	70	30	3	D2 21123
D2 21124	247	7	20	50	50	15	3,000	100	20L	5	D2 21124
D2 21122	145	5	20	50	100	10	2,000	100	30	3	D2 21122
D2 11796	133	10	N	100	79	20	3,000	200	100	7	D2 11796
D2 11797	142	7	20	20	63	15	7,000	150	70	5	D2 11797
D2 11798	225	N	N	30	207	15	10,000	150	70	5	D2 11798
D2 11799	228	10	N	70	136	15	10,000	150	70	5	D2 11799
D2 11800	253	50	20L	70	161	50	7,000	150	100	10	D2 11800
D2 21112	380	10	15	50	71	10	1,500	70	30	2	D2 21112
D2 21113	241	10	20	50	73	20	3,000	100	30	5	D2 21113
D2 21107	178	5	15	20	63	10	3,000	70	30	2	D2 21107
D2 21108	213	10	20	30	39	15	2,000	50	50	3	D2 21108
D2 21111	118	3	15	20	50	10	2,000	70	30	2	D2 21111
D2 21118	946	5	20	20	50	10	3,000	70	30	2	D2 21118
D2 21119	412	20	15	70	42	15	3,000	15L	50	3	D2 21119
D2 11788	144	20	N	100	68	30	5,000	150	70	7	D2 11788
D2 11789	189	20	20L	30	130	20	10,000	150	50	5	D2 11789
D2 11790	206	7	N	30	56	15	7,000	100	50	5	D2 11790
D2 11791	180	70	20	100	49	30	5,000	150	100	7	D2 11791
D2 11792	264	30	N	100	59	20	7,000	150	70	7	D2 11792
D2 11803	141	20	20	100	88	30	2,000	200	70	7	D2 11803
D2 11804	301	10	20L	50	90	20	7,000	150	50	5	D2 11804
D2 11805	251	100	20	50	179	20	7,000	150	50	5	D2 11805
D2 11806	326	100	20L	50	132	20	10,000	150	50	5	D2 11806
D2 11807	254	20	N	50	46	20	5,000	150	50	5	D2 11807
D2 11808	256	15	20	100	156	50	3,000	300	100	7	D2 11808
D2 21117	157	10	20	30	36	15	5,000	100	50	3	D2 21117
D2 21114	144	7	20	50	40	20	1,000	100	30	5	D2 21114
D2 21115	270	5	20	30	50	15	3,000	70	30	3	D2 21115

Table 5.--Major- and minor-oxide and trace-element composition of the laboratory ash of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--continued

Sample number	Zn (ppm)	Zr-S (ppm)
D2 2 1120	102	100
D2 1 1793	110	150
D2 2 1109	119	200
D2 1 1801	75	200
D2 1 1794	252	200
D2 2 1110	200	300
D2 1 1802	117	200
D2 2 1121	48	150
D2 1 1795	20L	200
D2 2 1116	40	500
D2 2 1123	76	200
D2 2 1124	112	500
D2 2 1122	143	200
D2 1 1796	82	200
D2 1 1797	49	500
D2 1 1798	83	300
D2 1 1799	85	300
D2 1 1800	95	300
D2 2 1112	70	150
D2 2 1113	141	300
D2 2 1107	75	200
D2 2 1108	69	200
D2 2 1111	67	200
D2 2 1118	51	200
D2 2 1119	151	200
D2 1 1788	135	300
D2 1 1789	71	300
D2 1 1790	84	300
D2 1 1791	190	200
D2 1 1792	193	200
D2 1 1803	55	300
D2 1 1804	53	300
D2 1 1805	87	300
D2 1 1806	122	300
D2 1 1807	126	200
D2 1 1808	162	300
D2 2 1117	87	200
D2 2 1114	90	300
D2 2 1115	83	300

Table 6.--Contents of nine trace elements in 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[Analyses in air-dried (32°C) coal, L, less than the value shown]

Sample number	As (ppm)	Co (ppm)	Cr (ppm)	F (ppm)	Hg (ppm)	Sb (ppm)	Se (ppm)	Th (ppm)	U (ppm)	Sample number
D2 21120	0.9	8.8	46	65	0.02	0.2	0.3	0.7	0.6	D2 21120
D2 11793	.5	8.8	37	40	.01	.2	.2	.4	.4	D2 11793
D2 21109	7.8	24	64	190	.04	.1L	.1L	2.5	.9	D2 21109
D2 18 01	.9	14	49	55	.04	.4	.4	.6	.5	D2 11801
D2 11794	24	30	88	49	.17	1.0	2.3	5.5	5.7	D2 11794
D2 21110	61	58	90	150	.27	1.6	2.7	4.4	4.9	D2 21110
D2 11802	22	19	61	60	.10	.6	1.2	1.1	1.7	D2 11802
D2 21121	.5	16	34	90	.01	.3	.3	1.1	.6	D2 21121
D2 11795	.5	7.8	34	65	.02	.2	.6	1.1	.2	D2 11795
D2 21116	19	8.9	52	60	.17	.8	1.0	2.2	1.3	D2 21116
D2 21123	.8	15	49	110	.03	1.9	.3	.7	.3	D2 21123
D2 21124	1.9	32	65	70	.21	.6	.7	1.2	1.0	D2 21124
D2 21122	1.4	17	61	75	.09	.3	.6	1.4	.9	D2 21122
D2 11796	2.1	15	52	70	.09	.4	.7	1.8	1.3	D2 11796
D2 11797	.4	8.3	51	30	.03	.2	.4	1.0	.3	D2 11797
D2 11798	.3	7.8	41	25	.02	.1	.1L	.6	.3	D2 11798
D2 11799	.7	13	43	20	.03	.1	.4	.7	.5	D2 11799
D2 11800	3.9	20	70	30	.05	.4	.3	.6	.4	D2 11800
D2 21112	1.8	21	44	30	.06	.2	.5	.6	.4	D2 21112
D2 21113	1.0	29	43	30	.04	.1	.3	.4	.2	D2 21113
D2 21107	1.6	15	46	45	.09	.2	.6	.9	.4	D2 21107
D2 21108	17	31	42	25	.06	.4	.4	.9	.6	D2 21108
D2 21111	8.5	11	55	75	.06	.3	.5	1.2	.5	D2 21111
D2 21118	.9	13	52	25	.05	.2	.4	.9	.5	D2 21118
D2 21119	4.0	64	50	35	.16	.3	.5	.5	.8	D2 21119
D2 11788	1.7	12	43	45	.10	.3	.5	1.1	.8	D2 11788
D2 11789	.4	12	49	40	.02	.1	.3	.6	.2L	D2 11789
D2 11790	.4	9.1	48	35	.02	.1	.2	.5	.2	D2 11790
D2 11791	1.9	27	48	45	.06	.4	.6	1.4	1.4	D2 11791
D2 11792	.7	38	42	40	.04	1.5	.2	.5	.3	D2 11792
D2 11803	5.5	15	65	55	.13	.6	.7	1.8	1.5	D2 11803
D2 11804	.4	12	40	50	.02	.1	.2	.5	.3	D2 11804
D2 11805	.3	12	2.3L	50	.02	.1	.3	.5	.2L	D2 11805
D2 11806	.4	10	49	45	.02	.1	.2	.5	.2	D2 11806
D2 11807	1.5	12	64	85	.05	.3	.7	1.5	1.3	D2 11807
D2 11808	6.6	20	76	70	.06	.6	.4	1.2	.7	D2 11808
D2 21117	.9	16	48	45	.05	.3	.6	8.1	.7	D2 21117
D2 21114	19	14	74	230	.07	1.1	.8	4.0	2.3	D2 21114
D2 21115	12	9.8	40	60	.27	.5	.8	1.8	.7	D2 21115

Table 7.--Major-, minor-, and trace-element composition of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[Values in percent or parts per million, As, Co, Cr, F, Hg, Sb, Se, Th, and U values are from direct determinations on air-dried (32°C) coal; all other values calculated from analyses of coal ash. S means analysis by emission spectrography; L, less than the value shown; N, not detected; B, not determined]

Sample number	Si (percent)	Al (percent)	Ca (percent)	Mg (percent)	Na (percent)	K (percent)	Fe (percent)	Ti (percent)	As (ppm)	B-S (ppm)	Sample number
D2 21120	0.62	0.25	0.57	0.19	0.40	0.024	0.19	0.015	0.9	30	D2 21120
D2 11793	.34	.24	.60	.30	.029	.014	.20	.010	.5	70	D2 11793
D2 21109	4.7	1.4	.47	.66	.13	.47	.54	.057	7.8	50	D2 21109
D2 11801	.54	.26	.54	.19	.30	.037	.19	.013	.9	100	D2 11801
D2 11794	5.6	2.6	.59	.27	.44	.32	2.2	.099	24	50	D2 11794
D2 21110	3.7	1.6	.37	.42	.090	.24	2.4	.062	61	70	D2 21110
D2 11802	1.1	.54	.48	.23	.18	.070	1.7	.022	22	70	D2 11802
D2 21121	.65	.50	.59	.14	.45	.006	.12	.016	.5	30	D2 21121
D2 11795	1.1	.61	.66	.068	.27	.014	.15	.028	.5	70	D2 11795
D2 21116	3.8	.67	.43	.17	.064	.051	.41	.055	19	50	D2 21116
D2 21123	.71	.41	.61	.22	.13	.020	.17	.017	.8	30	D2 21123
D2 21124	1.3	.45	.59	.19	.22	.013	.28	.045	1.9	30	D2 21124
D2 21122	1.8	.70	.53	.12	.42	.083	.30	.041	1.4	20	D2 21122
D2 11796	1.9	.88	.65	.14	.50	.068	.47	.037	2.1	50	D2 11796
D2 11797	1.3	.45	.63	.12	.52	.007	.17	.051	.4	50	D2 11797
D2 11798	.70	.32	.54	.11	.45	.011	.20	.018	.3	50	D2 11798
D2 11799	.51	.29	.51	.11	.44	.012	.20	.015	.7	50	D2 11799
D2 18800	.50	.28	.51	.097	.42	.011	.28	.015	3.9	70	D2 18800
D2 21112	.56	.32	.47	.28	.052	.009	.23	.015	1.8	30	D2 21112
D2 21113	.37	.26	.50	.21	.042	.014	.20	.011	1.0	30	D2 21113
D2 21107	.85	.39	.51	.085	.42	.014	.19	.025	1.8	30	D2 21107
D2 21108	1.1	.35	.42	.001L	.38	.011	.31	.027	17	50	D2 21108
D2 21111	1.5	.57	.49	.092	.38	.069	.20	.038	8.5	30	D2 21111
D2 21118	.78	.39	.62	.14	.12	.016	.32	.022	.9	30	D2 21118
D2 21119	.29	.18	.36	.071	.38	.008	.26	.009	4.0	30	D2 21119
D2 11788	.97	.55	.76	.21	.092	.012	.26	.023	1.7	50	D2 11788
D2 11789	.59	.35	.73	.20	.098	.008	.17	.025	.4	50	D2 11789
D2 11790	.48	.25	.70	.18	.10	.004	.14	.016	.4	70	D2 11790
D2 11791	.74	.68	.62	.17	.11	.012	.26	.019	1.9	70	D2 11791
D2 11792	.42	.22	.54	.12	.24	.011	.17	.013	.7	70	D2 11792
D2 11803	1.5	.71	.65	.26	.062	.027	.36	.035	5.5	70	D2 11803
D2 11804	.49	.31	.67	.26	.073	.005	.12	.022	.4	70	D2 11804
D2 11805	.48	.34	.66	.24	.098	.009	.12	.021	.3	70	D2 11805
D2 11806	.45	.24	.61	.22	.11	.008	.11	.015	.4	70	D2 11806
D2 11807	1.2	.62	.60	.23	.15	.070	.21	.026	1.5	70	D2 11807
D2 11808	1.7	.60	.51	.17	.28	.11	.34	.031	6.6	100	D2 11808
D2 21117	.70	.36	.45	.042	.37	.012	.22	.018	1.9	50	D2 21117
D2 21114	6.9	2.4	.51	.87	.44	.75	.90	.095	19	70	D2 21114
D2 21115	1.5	.83	.45	.057	.31	.055	.39	.045	12	50	D2 21115

Table 7.--Major-, minor-, and trace-element composition of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--continued

Sample number	Ba-S (ppm)	Be-S (ppm)	Cd (ppm)	Ce-S (ppm)	Co (ppm)	Cr (ppm)	Cu (ppm)	F (ppm)	Ga-S (ppm)	Ge-S (ppm)	Sample number
D221120	150	0.15	0.05L	20L	8.8	46	4.4	65	0.7	0.15	D221120
D211793	200	.15	.22	N	8.8	37	3.6	40	2	N	D211793
D221109	200	1	.17L	100L	24	64	9.0	190	3	1	D221109
D211801	500	1	.20	N	14	49	4.3	55	2	N	D211801
D211794	1,500	3	1.9	N	30	88	55	49	15	5	D211794
D221110	500	2	.18	100L	58	90	43	150	5	1.5	D221110
D211802	700	2	.10	N	19	61	10	60	5	N	D211802
D221121	200	.3	.06L	5	16	34	4.4	90	1.5	.2	D221121
D211795	500	.7	.29	N	7.8	34	3.5	65	3	N	D211795
D221116	300	1	.13	15	8.9	52	11	60	2	2	D221116
D221123	200	.15	.05L	20L	15	49	5.1	110	1.5	.2	D221123
D221124	300	.7	.07L	30L	32	65	8.7	70	1	.3	D221124
D221122	300	.2	.09L	50L	17	61	8.8	75	2	.5	D221122
D211796	700	.3L	.53	N	15	52	9.4	70	3	N	D211796
D211797	1,000	N	.71	N	8.3	51	7.7	30	2	N	D211797
D211798	700	N	.49	N	7.8	41	4.5	25	1.5	N	D211798
D211799	700	.2	.05	N	13	43	4.6	20	1.5	N	D211799
D211800	300	1	.05	N	20	70	4.7	30	3	N	D211800
D221112	200	.15	.05L	20L	21	44	4.7	30	1	.2	D221112
D221113	300	.5	.04L	20L	29	43	3.3	30	1	.1	D221113
D221107	300	.2	.06L	30L	15	46	4.7	45	1	.15	D221107
D221108	100	.7	.06L	30L	31	42	4.7	25	1	.2	D221108
D221111	200	.2	.08L	50L	11	55	7.0	75	1	.3	D221111
D221118	200	.15	.06L	30L	13	52	5.2	25	.7	.2	D221118
D221119	150	.5	.04L	5	64	50	4.1	35	1	.15	D221119
D211788	500	.2	.41	N	12	43	6.8	45	3	N	D211788
D211789	300	N	1.6	N	12	49	6.4	40	1.5	N	D211789
D211790	500	N	.22	N	9.1	48	3.3	35	1.5	N	D211790
D211791	500	.3	.50	N	27	48	5.1	45	3	N	D211791
D211792	300	.5	.50	N	38	42	3.6	40	1.5	N	D211792
D211803	700	.5	.17	N	15	65	9.7	55	5	7	D211803
D211804	700	N	.05L	N	12	40	4.7	50	1.5	N	D211804
D211805	700	N	.09	N	12	2.3L	4.9	50	1.5	N	D211805
D211806	700	N	.04	N	10	49	3.5	45	1.5	N	D211806
D211807	500	N	.07	N	12	64	6.7	85	2	N	D211807
D211808	700	1.5	.17	N	20	76	7.9	70	7	N	D211808
D221117	200	.3	.05L	30L	16	48	5.3	45	1.5	.7	D221117
D221114	700	2	.26	150L	14	74	16	230	30	5L	D221114
D221115	500	1	.34	50L	9.8	40	7.4	60	3	.5	D221115

Table 7.--Major-, minor-, and trace-element composition of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--continued

Sample number	Hg (ppm)	La-S (ppm)	Li (ppm)	Mn (ppm)	Mo-S (ppm)	Nb-S (ppm)	Ni-S (ppm)	P (ppm)	Pb (ppm)	Sb (ppm)	Sample number
D221120	0.02	1.5	1.6	19	0.7	0.7	1	260	5.1	0.2	D221120
D211793	.01	N	1.1	19	3	N	2	43L	6.7	.2	D211793
D221109	.04	10	8.8	35	.7	3	7	45L	4.3L	.1L	D221109
D211801	.04	N	2.0	20	1	N	2	88	5.4	.4	D211801
D211794	.17	30L	25	38	15	N	50	830	15	1.0	D211794
D221110	.27	15	19	23	5	5	15	88	7.3	1.6	D221110
D211802	.10	10L	4.1	29	7	N	20	130	5.3	.6	D211802
D221121	.01	3	2.5	17	.3	1	3	1,200	2.2	.3	D221121
D211795	.02	N	2.8	11	1	N	2	570	3.7	.2	D211795
D221116	.17	7	.1	12	1.5	5	5	570	3.3L	.8	D221116
D221123	.0	2	3.1	13	.3	1.5	1.5	87	2.4	1.9	D221123
D221124	.21	3	3.7	18	.5	1.5	3	180	3.6	.6	D221124
D221122	.09	5	5.6	13	.5	2	3	170	8.8	.3	D221122
D211796	.09	10L	9.2	14	1	N	10	310	8.4	.4	D211796
D211797	.03	N	4.9	10	.5	1.5	1.5	170	4.5	.2	D211797
D211798	.02	N	2.5	12	N	N	1.5	87	11	.1	D211798
D211799	.03	5L	2.8	12	.5	N	3	45	6.9	.1	D211799
D211800	.05	N	1.9	14	3	1L	3	45L	8.7	.4	D211800
D221112	.06	2	1.9	18	.5	.7	2	43	3.3	.2	D221112
D221113	.04	2	.8	10	.5	1	1.5	44L	3.1	.1	D221113
D221107	.09	2	3.1	10	.3	1	1.5	87	3.6	.2	D221107
D221108	.06	2	2.5	13	.5	1	2	43L	2.4	.4	D221108
D221111	.06	3	4.4	9.1	.3	1.5	1.5	87	3.9	.3	D221111
D221118	.05	2	3.6	53	.3	1	1.5	88	2.8	.2	D221118
D221119	.16	1.5	1.8	17	1	.7	3	44	1.8	.3	D221119
D211788	.10	N	6.5	9.9	1.5	N	7	440	4.7	.3	D211788
D211789	.02	N	2.4	9.3	1	1L	1.5	88	6.4	.1	D211789
D211790	.02	N	1.1	9.1	.3	N	1.5	44	2.5	.1	D211790
D211791	.06	7L	8.1	11	5	1.5	7	260	3.0	.4	D211791
D211792	.04	N	1.7	12	1.5	N	5	220	2.7	1.5	D211792
D211803	.13	10L	8.8	12	1.5	1.5	10	220	7.6	.6	D211803
D211804	.02	N	.5	14	.5	1L	2	43L	4.1	.1	D211804
D211805	.02	N	2.4	11	5	1	2	44L	7.9	.1	D211805
D211806	.02	N	1.4	13	5	.7L	2	43L	5.4	.1	D211806
D211807	.05	N	4.5	19	1.5	N	3	390	3.4	.3	D211807
D211808	.06	N	3.4	22	1.5	1.5	10	44L	13	.6	D211808
D221117	.05	3	3.0	8.5	.5	1	2	220	1.9	.3	D221117
D221114	.07	10	15	37	1.5	7	10	90	10	1.1	D221114
D221115	.27	5	7.9	23	.5	1.5	2	170	4.3	.5	D221115

Table 7.--Major-, minor-, and trace-element composition of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--continued

Sample number	Sc-S (ppm)	Se (ppm)	Sr-S (ppm)	Th (ppm)	U (ppm)	V-S (ppm)	Y-S (ppm)	Yb-S (ppm)	Zn (ppm)	Zr-S (ppm)	Sample number
D2 21120	0.3	0.3	150	0.7	0.6	3	1.5	0.07	5.3	7	D2 21120
D2 11793	1	.2	150	.4	.4	7	3	.2	4.7	7	D2 11793
D2 21109	3	.1L	100	2.5	.9	15	7	.7	21	30	D2 21109
D2 11801	1.5	.4	200	.6	.5	7	3	.3	3.7	10	D2 11801
D2 11794	7	2.3	500	5.5	5.7	150	30	3	67	50	D2 11794
D2 21110	5	2.7	100	4.4	4.9	30	10	1	37	50	D2 21110
D2 11802	5	1.2	200	1.1	1.7	50	15	1.5	11	20	D2 11802
D2 21121	.7	.3	.7L	1.1	.6	1L	2	.15	2.8	7	D2 21121
D2 11795	1.5	.6	500	1.1	.2	10	7	.5	1.5L	15	D2 11795
D2 21116	2	1.0	200	2.2	1.3	15	7	.7	5.2	70	D2 21116
D2 21123	.5	.3	.5L	.7	.3	3	1.5	.15	3.9	10	D2 21123
D2 21124	1.5	.7	200	1.2	1.0	7	1.5L	.3	8.1	30	D2 21124
D2 21122	1	.6	200	1.4	.9	10	3	.3	13	15	D2 21122
D2 11796	2	.7	300	1.8	1.3	20	10	.7	8.7	20	D2 11796
D2 11797	1	.4	500	1.0	.3	10	5	.3	3.5	30	D2 11797
D2 11798	.7	.1L	500	.6	.3	7	3	.3	4.5	15	D2 11798
D2 11799	.7	.4	500	.7	.5	7	3	.2	4.3	15	D2 11799
D2 11800	3	.3	300	.6	.4	7	5	.5	5.1	15	D2 11800
D2 21112	.7	.5	70	.6	.4	3	1.5	.1	3.3	7	D2 21112
D2 21113	1	.3	150	.4	.2	5	1.5	.2	5.9	10	D2 21113
D2 21107	.7	.6	200	.9	.4	3	2	.15	4.3	10	D2 21107
D2 21108	1	.4	150	.9	.6	3	3	.2	4.3	15	D2 21108
D2 21111	.7	.5	200	1.2	.5	7	2	.2	5.2	20	D2 21111
D2 21118	.5	.4	150	.9	.5	5	1.5	.1	2.9	10	D2 21118
D2 21119	.7	.5	150	.5	.8	.7L	2	.15	6.3	10	D2 21119
D2 11788	2	.5	300	1.1	.8	10	5	.5	9.3	20	D2 11788
D2 11789	1	.3	500	.6	.2L	7	2	.2	3.5	15	D2 11789
D2 11790	.7	.2	300	.5	.2	5	2	.2	3.7	15	D2 11790
D2 11791	2	.6	300	1.4	1.4	10	7	.5	12	15	D2 11791
D2 11792	1	.2	300	.5	.3	7	3	.3	8.7	10	D2 11792
D2 11803	2	.7	150	1.8	1.5	15	7	.7	4.7	20	D2 11803
D2 11804	1	.2	300	.5	.3	7	2	.2	2.4	15	D2 11804
D2 11805	1	.3	300	.5	.2L	7	2	.2	3.8	15	D2 11805
D2 11806	.7	.2	500	.5	.2	7	2	.2	5.0	15	D2 11806
D2 11807	1.5	.7	300	1.5	1.3	10	3	.3	9.2	15	D2 11807
D2 11808	5	.4	200	1.2	.7	20	10	.7	15	20	D2 11808
D2 21117	.7	.6	200	8.1	.7	7	2	.15	4.7	15	D2 21117
D2 21114	5	.8	200	4.0	2.3	30	10	1	23	70	D2 21114
D2 21115	1	.8	200	1.8	.7	7	3	.3	7.1	30	D2 21115

Table 8.--Elements looked for but not detected in 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[Approximate lower detection limits for these elements in ash, by the six-step spectrographic method of the U.S. Geological survey, are included]

Element name	Symbol	Lower limit of detection (ppm) in ash
Silver	Ag	1
Gold	Au	50
Bismuth	Bi	20
Dysprosium	Dy	100
Erbium	Er	100
Europium	Eu	200
Gadolinium	Gd	100
Hafnium	Hf	200
Holmium	Ho	50
Indium	In	20
Lutetium	Lu	70
Palladium	Pd	5
Praseodymium	Pr	200
Platinum	Pt	100
Rhenium	Re	100
Samarium	Sm	200
Tin	Sn	20
Tantalum	Ta	1,000
Terbium	Tb	700
Tellerium	Te	5,000
Thallium	Tl	100
Thulium	Tm	50
Tungsten	W	200

Table 9.--Arithmetic mean, observed range, geometric mean, and geometric deviation of proximate and ultimate analyses, heat of combustion, forms of sulfur, and ash-fusion temperatures of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[For comparison, geometric means for 33 Powder River region coal samples are included (Swanson and others, 1976, tables 31b and 32b). All values are in percent except Kcal/kg, Btu/lb, ash-fusion temperatures, and geometric deviations, and are reportedon the as-received basis. L, less than the value shown. Leaders (---) indicate no data. $^{\circ}F = (^{\circ}C \times 1.8) + 32$]

	Arithmetic mean	Observed range		Geometric mean	Geometric deviation	Powder River region geometric mean
		Minimum	Maximum			
Proximate and ultimate analyses						
Moisture	25.2	16.6	30.6	25.0	1.1	23.1
Volatile matter	28.9	25.1	32.0	28.9	1.1	32
Fixed carbon	39.3	30.6	45.5	39.2	1.1	36
Ash	6.4	2.8	23.7	5.5	1.7	7.5
Hydrogen	6.2	5.1	6.7	6.2	1.1	6.2
Carbon	51.0	40.0	57.1	50.9	1.1	50.3
Nitrogen	.8	.7	1.1	.8	1.1	.9
Oxygen	38.5	.6	39.4	31.1	1.9	32.9
Sulfur	.6	.2	3.2	.5	1.9	.8
Heat of combustion						
Kcal/kg	4,875	3,885	5,445	4,870	1.1	4,860
Btu/lb	8,770	6,990	9,790	8,760	1.1	8,740
Forms of sulfur						
Sulfate	0.02	0.01L	0.26	0.01	2.3	0.02
Pyritic	.17	.02	1.91	.10	2.7	.29
Organic	.43	.15	1.17	.37	1.7	.31
Ash-fusion temperatures, °C						
Initial deformation	1,120	1,010	1,290	1,120	1.1	---
Softening temperature	1,170	1,060	1,350	1,170	1.1	---
Fluid temperature	1,220	1,120	1,390	1,220	1.1	---

Table 10.--Arithmetic mean, observed range, geometric mean, and geometric deviation of ash content and contents of nine major and minor oxides in the laboratory ash of 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[For comparison, geometric means for 410 Powder River region samples are included (Hatch and Swanson, 1977, table 6a). All samples were ashed at 525°C; all analyses except geometric deviation are in percent. L, less than the value shown. Leaders (---) indicate no data]

Oxide	Arithmetic mean	Observed range		Geometric mean	Geometric deviation	Powder River region geometric mean
		Minimum	Maximum			
(Ash)	7.8	4.1	26.7	6.9	1.6	9.0
SiO_2	32	15	62	30	1.4	28
Al_2O_3	13	8.0	21	13	1.3	14
CaO	13	2.8	22	11	1.7	15
MgO	4.8	1.1L	11	3.9	1.9	3.6
Na_2O	5.4	.66	12	3.7	2.4	.93
K_2O	.62	.12	3.5	.42	2.4	.28
Fe_2O_3	6.2	2.9	24	5.7	1.5	5.8
TiO_2	.62	.37	1.2	.60	1.3	.61
P_2O_5	.68	.08L	4.6	.28	3.9	---

Table 11.--Arithmetic mean, observed range, geometric mean, and geometric deviation of 39 elements in 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana

[For comparison, geometric means for 410 Powder River region coal samples are included (Hatch and Swanson, 1977, table 6b). All analyses except geometric deviation are in percent or parts per million and are reported on a whole-coal basis. As, Co, Cr, F, Hg, Sb, Se, Th, and U values used to calculate the statistics were determined directly on whole coal. All other values used were calculated from determinations made on coal ash. L, less than the value shown. Leaders (---) indicate no data]

Element	Arithmetic mean	Observed range		Geometric mean	Geometric deviation	Powder River region geometric mean
		Minimum	Maximum			
	Percent					
Si	1.3	0.29	6.9	.97	2.2	1.2
Al	.58	.18	2.6	.47	1.9	.66
Ca	.56	.36	.75	.55	1.2	.98
Mg	.201	.041L	.87	.16	1.9	.20
Na	.27	.028	.52	.19	2.3	.063
K	.054	.004	.75	.024	3.6	.022
Fe	.36	.11	2.4	.27	2.1	.37
Ti	.030	.009	.099	.024	1.8	.035
P	.020	.004L	.12	.010	3.3	---
	Parts per million					
As	5.6	0.3	61	1.9	4.3	2
B	50	20	100	50	1.5	50
Ba	500	100	1500	500	1.9	300
Be	.7	.3L	3	.3	3.2	.5
Cd	.3	.04L	1.8	.07	5.6	.04
Co	18	7.7	64	15	1.7	2
Cr	52	33	90	50	1.3	5
Cu	7.7	3.3	55	6.4	1.8	9.5
F	60	20	230	52	1.7	40
Ga	3	.7	30	2	2.2	2
Ge	.5	.1L	7	.1	7.2	---
Hg	.07	.01	.27	.05	2.4	.08
La	2	1.5L	15	1.5	3.1	---
Li	4.9	.1	25	3.2	2.6	3.9
Mn	17	8.4	52	15	1.6	34
Mo	1.5	.3L	15	1	2.9	1.5
Nb	1.5	.7L	7	1	2.5	1.0
Ni	5	1	50	3	2.4	3
Pb	5.3	1.7L	14	4.4	1.8	5.1
Sb	.4	.1L	1.9	.3	2.6	.4

Table 11.--Arithmetic mean, observed range, geometric mean, and geometric deviation of 39 elements in 39 coal samples from the Fort Union Formation, Prairie Dog Creek study area, Rosebud County, Montana--Continued

Element	Arithmetic mean	Observed range		Geometric mean	Geometric deviation	Powder River region geometric mean
		Minimum	Maximum			
	Parts per million					
Sc	1.5	0.3	7	1.5	2.1	1.5
Se	.6	.2L	2.7	.4	2.0	.7
Sr	300	.7L	500	150	2.2	150
Th	1.4	.4	8.1	1.1	2.1	3.3
U	.9	.2L	5.7	.6	2.4	.6
V	15	3L	150	7	2.3	10
Y	5	1.5L	30	3	2.2	3
Yb	.5	.07	3	.3	2.2	.3
Zn	8.4	2.4L	67	6.3	2.1	12.5
Zr	20	7	70	15	1.8	15

To be consistent with the precision of the semiquantitative emission spectrographic technique, arithmetic and geometric means of elements determined by this method are reported as the midpoints of the enclosing six-step brackets. For an explanation of six-step brackets, see headnote of table 5, or see Swanson and Huffman, 1976, p. 6.

Explanation of statistical terms used in summary tables

In this report the geometric mean (GM) is used as the estimate of the most probable concentration (mode); the geometric mean is calculated by taking the logarithm of each analytical value, summing the logarithms, dividing the sum by the total number of values, and obtaining the antilogarithm of the result. The measure of scatter about the mode used here is the geometric deviation (GD), which is the antilog of the standard deviation of the logarithms of the analytical values. These statistics are used because the quantities of trace elements in natural materials commonly exhibit positively skewed frequency distributions; such distributions are normalized by analyzing and summarizing trace-element data on a logarithmic basis.

If the frequency distributions are lognormal, the geometric mean is the best estimate of the mode, and the estimated range of the central two-thirds of the observed distribution has a lower limit equal to GM/GD and an upper limit equal to GM*GD. The estimated range of the central 95 percent of the observed distribution has a lower limit equal to GM/GD^2 and an upper limit equal to $GM*GD^2$ (Connor and others, 1976).

Although the geometric mean is, in general, an adequate estimate of the most common analytical value, it is, nevertheless, a biased estimation of the arithmetic mean. The estimates of the arithmetic means listed in the summary tables are Sichel's $\underline{t}$ statistic (Miesch, 1967).

A common problem in statistical summaries of trace-element data arises when the element content of one or more of the samples is below the limit of analytical detection. This results in a "censored" distribution. Procedures developed by Cohen (1959) were used to compute unbiased estimates of the geometric mean, geometric deviation, and arithmetic mean when the data were censored.

Regional statistical comparison of composition of Prairie Dog Creek coal

Using the geometric means shown in tables 9, 10, and 11, the analytical data from the 39 samples of coal from the Prairie Dog Creek study area can be compared statistically with analytical data from coal beds in the surrounding Powder River region of Montana and Wyoming. The following comparisons use the student's t test at the 95-percent confidence level.

Coal from the Prairie Dog Creek study area has significantly higher contents of moisture and fixed carbon, and significantly lower contents of volatile matter, ash, nitrogen, total sulfur, sulfate sulfur, and pyritic sulfur than coal from 33 regional samples (table 9). The heat of combustion and the contents of hydrogen, carbon, oxygen, and organic sulfur are not significantly different. When compared at the 99-percent confidence level, the contents of moisture, nitrogen, and sulfur are not significantly different.

Coal from the Prairie Dog Creek study area has significantly higher contents of Na_2O and K_2O, and significantly lower contents of ash and CaO content in the ash than coal from 410 regional samples (table 10). The contents of SiO_2, Al_2O_3, MgO, Fe_2O_3, and TiO_2 are not significantly different. When compared at the 99-percent confidence level, the content of K_2O is not significantly different.

Coal from the Prairie Dog Creek study area has significantly higher contents of Na, Ba, Cd, Co, Cr, and F, and significantly lower contents of Al, Ca, Mg, Fe, Ti, Be, Cu, Hg, Mn, Se, Th, V, and Zn than coal from 410 regional samples (table 11). The contents of Si, K, As, B, Ga, Li, Mo, Nb, Ni, Pb, Sb, Sc, Sr, U, Y, Yb, and Zr are not significantly different. When compared at the 99-percent confidence level, the contents of Fe and F are not significantly different.

Differences in the oxide composition of coal ashes and the elemental contents of coal result from differences in the total and relative amounts of the various inorganic minerals, the elemental composition of these minerals, and the total and relative amounts of any organically bound elements. The chemical form and distribution of a given element are dependent on the geologic history of the coal bed. A partial listing of the factors that influence element distributions would include chemical composition of original plants; amounts and composition of the various detrital, diagenetic, and epigenetic minerals; chemical characteristics of the ground waters that come in contact with the bed; temperatures and pressures during burial; and extent of weathering. No evaluation of these factors has been made for coal from the Prairie Dog Creek study area.

Composition of Prairie Dog Creek coals, by bed

The 39 samples of coal were taken from six coal beds in the Prairie Dog Creek study area. Twenty-seven samples are from the Wall bed, and, of these, 16 samples were taken from three localities (D, L, and N) at which the Wall was sampled in detail to determine variations of composition within the coal bed (fig. 2). On the average, the Wall coal is low in sulfur and ash (table 12) and has a heating value of 9200 Btu/lb (5210 kcal/kg) on an as-received basis. When calculated on a moist-mineral-matter-free basis, the heating value indicates an apparent rank for the Wall bed of subbituminous B. The

detailed sampling of the bed indicates that the middle part of the Wall is remarkably low in sulfur and ash content, being about 0.2 percent sulfur and 3 percent ash on an as-received basis. The uppermost and lowermost samples have a sulfur content of 0.5 to 0.7 percent and an ash content ranging from 3.2 to 6.7 percent. The heating value of individual samples ranges from 8420 to 9790 Btu/lb (4770 to 5510 kcal/kg) on an as-received basis. The highest heating values for the bed as a whole are in the south and east (localities Q, G, and I).

Four analyses of the Canyon coal bed (table 4) show a sulfur content of 0.4 to 0.5 percent, a variable ash content ranging from 3.2 to 15.4 percent, and a heating value ranging from 7850 to 8550 Btu/lb (4450 to 4840 kcal/kg) on an as-received basis. Its apparent rank is subbituminous C.

Table 12.--Average heat of combustion, moisture, ash and sulfur content on an as-received basis, and apparent rank, by 39 coal bed, of coal samples from the Prairie Dog Creek study area, Rosebud County, Montana

[To convert Btu/lb to Kcal/kg divide by 1.8]

Coal bed	No. of samples	Moisture	Ash	Sulfur	Heat-of-combustion Btu/lb.	Moist mineral matter-free heat content	Apparent coal rank
Canyon	4	27.6	6.6	.5	8,360	9,020	Subbituminous C
Sub Canyon	3	24.4	13.5	2.7	7,720	9,100	Do.
Cook	3	26.4	8.0	.6	8,380	9,190	Do.
Wall	15	24.2	4.9	.5	9,200	9,730	Subbituminous B
Upper Wall	8	24.0	5.4	.3	9,100	9,680	Do.
Lower Wall	4	23.0	5.0	.6	9,300	9,850	Do.
Carlson	1	16.6	23.7	1.2	7,600	10,300	Do.
Brewster-Arnold	1	24.4	7.8	.7	8,760	9,590	Do.

Two samples of the Cook coal bed show a low sulfur and low ash content of 0.4 and 5.4 percent respectively, but the third sample is relatively high in ash and moderate in sulfur (table 4). The sub-Canyon bed has a relatively high ash content of 13.5 percent, a moderate sulfur content of 2.7 percent, and an apparent rank of subbituminous C, according to the as-received analyses of three samples.

The single samples of two of the beds (fig. 1) below the Wall show a high ash and moderate sulfur content for the Carlson, and a moderate ash and low sulfur content for the Brewster-Arnold on an as-received basis. The apparent rank, however, is subbituminous B for both beds.

Estimation and classification of coal resources

In preparing the coal resource estimates for the Prairie Dog Creek study area, the procedures and definitions used were those of the Coal Resources Classification System of the U.S. Bureau of Mines and the U.S. Geological Survey (1976), which is published as U.S. Geological Survey Bulletin 1450-B.

The term "coal resources," as used herein, designates the estimated quantity of coal in the ground in such form that economic extraction is currently or potentially feasible. Identified resources are specific bodies of coal whose location, rank, quality, and quantity are known from geologic evidence supported by engineering measurements.

Tabulation of coal resources

In the study area, identified coal resources that have potential for recovery by surface mining methods are assumed to be coal within 200 feet (60 m) of the surface for the Canyon bed, or within 500 feet of the surface for the Thick Wall bed. As such, these coal resources fall into a category called reserve base, which is defined as that part of the identified coal resource from which reserves are calculated. Reserves are the actual amount of coal that can be economically mined from a deposit at the time of determination considering all legal, technological, and environmental restraints, and they are derived by applying a percent recovery factor to the reserve base. The recovery factor takes into account all coal remaining in the ground after mining is completed (considered to be "lost in mining") and includes coal (1) left unmined beneath rivers, lakes, highways, and legal reservations; (2) left unmined adjacent to mine or property boundaries; or (3) left unmined because of environmental, quality, safety, hydrologic, or legal restrictions.

In the United States, the recovery factor for surface mining methods locally exceeds 90 percent. Because of the many uncertainties about legal and other restrictions on surface mining, no recovery factor was applied to the reserve base coal in the study area.

Characteristics used in resource evaluation

The characteristics used in evaluating resources can be divided into two main classes: (1) those that affect the utilization and the economic feasibility of recovery of coal, and (2) those that characterize the coal resources in terms of the degree of geologic assurance that the coal resources exist in the amount stated. Such factors as rank, grade, and density of the coal, and the depth and thickness of the bed affect the economic feasibility of recovery and utilization of the coal. The rank and the grade of the coal in the study area have been discussed previously.

Density

The density, or weight per unit volume, of the coal varies considerably with differences in rank and ash content. In the Prairie Dog Creek study area, the density or specific gravity of the coals has not been determined so an average density or specific gravity is used, based on determinations from other areas. For subbituminous coal the average density is taken as 1,770 short tons per acre-foot, and the average specific gravity as 1.30.

Thickness of coal beds

Because of the importance of the thickness of the coal in determining the economic feasibility of recovery, most coal resource estimates prepared by the U.S. Geological Survey are tabulated according to three thickness categories. For subbituminous coal the categories are (1) thin, 2.5-5 feet (0.75-1.5 m), (2) intermediate, 5-10 feet (1.5-3 m), and (3) thick, more than 10 feet (3 m). In the Prairie Dog Creek study area, all of the resources tabulated in the Wall coal bed are in the thick category, the resources for the Canyon coal bed are both intermediate and thick, and the resources in the Cook bed are intermediate and thin (pls. 2, 3, and 4).

Depth of coal beds

Coal resources are commonly divided into categories based on the depth of the coal bed, as follows: 0-1,000 feet (0-300 m), 1,000-2,000 feet (300-600 m), 2,000-3,000 feet (600-900 m), and 3,000-6,000 feet (900-1,800 m). Additional categories of depth for coal resources that can be recovered by surface mining methods are not standardized, because of the many factors that affect the amount of overburden that can be economically removed from a coal deposit. In this area it is assumed that the Canyon and Cook coal beds to a depth of 200 feet (61 m) and the Wall bed to a depth of 500 feet (152 m) can be economically mined by surface-mining methods.

Resource categories according to degree of geologic assurance

The coal resources tabulated for the Prairie Dog Creek study area are all in the "Identified" category of geologic assurance, and are subdivided into "Measured," "Indicated," and "Inferred" categories according to the nearness of the coal to a measurement of the coal bed, and on geologic evidence and projection.

Measured -- Coal for which estimates of the rank, quality, and quantity have been computed, with a margin of error of less than 20 percent, from sample analyses and measurements from closely spaced and geologically well-known sample sites. In this area measured coal is within 1/4 mile (0.4 km) of a measurement in a drill hole or outcrop.

Indicated-- Coal for which estimates of the rank, quality, and quantity have been computed partly from sample analysis and measurements and partly from reasonable geologic projections. In this area, indicated coal is the body of coal whose inner limit is 1/4 mile (0.4 km) from a measurement in a drill hole or outcrop and whose outer limit is 3/4 mile (1.2 km) from the measurement.

Inferred -- Coal in unexplored extensions of indicated resources for which estimates of the quality and size are based on geologic evidence and projection. In this area, inferred coal lies more than 3/4 mile (1.2 km) from a measurement in a drill hole or outcrop, but not more than 3 miles (4.8 km).

Demonstrated--A collective term for the sum of coal in both measured and indicated resources and reserves.

Summary of coal resources

The Wall coal bed contains 360 million short tons (327 million metric tons) of potentially surface-minable subbituminous B coal under less than 200 feet (61 m) of overburden, and an additional 284 million tons (258 million metric tons) under 200-500 feet (61-152 m) of overburden (table 13). The coal ranges in thickness from 31.5 to 62.5 feet (9.6 to 19.1 m), excluding all partings. The coal thickness includes Upper and Lower Wall where the Wall is separated into two beds. About 73 percent of the total Wall coal resources is Demonstrated reserve base; the remainder is Inferred reserve base.

The thinnest of the three beds, the Cook, contains a total of 25.9 million short tons (23.5 million metric tons) where the overburden is less than 200 feet (61 m) thick. The coal ranges in thickness from 2.1 to 3.6 feet (0.6 to 2.6 m) but no resources were calculated for thicknesses less than 2.5 feet (0.8 m). About 65 percent of the resources are in the "thin" category of 2.5 to 5.0 feet (0.8 to 1.5 m).

The Canyon coal bed, which is 4.5 to 15.5 feet (1.4 to 4.7 m) thick, contains 35.3 million short tons (32 million metric tons) of subbituminous C coal under less than 200 feet (61 m) of overburden (table 13). Of this amount, 65 percent is classified as Demonstrated reserve base and the remainder is Inferred reserve base. About one-third is in coal more than 10 feet (3 m) thick, mainly in the northwest part of the study area.

The Cook and Canyon are locally valuable as individual beds, and their occurrence within practical mining distance of the Wall provides incentive to mine the Wall under thick overburden. If 500 feet (153 m) of overburden were removed from the Wall, the tabulated resources of the Wall, Cook, and Canyon

Table 13.--Identified resources of potentially surface-minable coal in three beds in the Fort Union Formation, Prairie Dog Creek study area, T. 6 S., R. 41 E., Rosebud County, Montana, as of 1/1/80

[In millions of short tons. 1 short ton = 0.907 metric tons; 1 ft = 0.305 m. Totals rounded to three significant figures. Leaders (---) indicate no data]

	Demonstrated									
	Measured			Indicated			Inferred			
	Coal thickness in feet			Coal thickness in feet			Coal thickness in feet			
Coal Bed	2.5-5	5-10	>10	2.5-5	5-10	>10	2.5-5	5-10	>10	Total
0-200 feet of overburden										
Canyon	.13	2.95	1.61	---	13.9	4.55	---	6.42	5.88	35.3
Cook	4.55	2.47	---	8.33	5.51	---	3.96	1.12	---	25.9
Wall	---	---	83.7	---	---	199.	---	---	77.0	360.
Total	4.68	5.42	85.3	8.33	19.4	204.	3.96	7.54	82.9	421.
200-500 feet of overburden										
Wall	---	---	29.6	---	---	159.	---	---	95.8	284.
Total	---	---	29.6	---	---	159.	---	---	95.8	284.
Grand total	4.68	5.42	115.	8.33	19.4	363.	3.96	7.54	179.	705.

beds (table 13) could be recovered, plus an estimated 10 to 15 million tons (9-14 million metric tons) where the overburden is greater than 200 feet (61 m) thick on the Canyon and Cook beds, for a total of 715 to 720 million tons (648-653 million metric tons). Additional resources might be obtained from the sub-Canyon and local beds, but none were calculated because of the relatively high sulfur content of the sub-Canyon and because of the sparse information available on the thickness and quality of the local beds.

The coal beds underlying the Wall (fig. 1) are considered to be either too thin, of poor quality, or too deep to be considered as potentially minable coal deposits in the Prairie Dog Creek study area, so no resources were calculated for them.

References cited

American Society for Testing and Materials, 1977, Standard specifications for classification of coals by rank (ASTM designation D-388-77): 1977 Annual Book of ASTM standards, pt. 26, p. 214-218.

Baker, A. A., 1929, The northward extension of the Sheridan coal field, Big Horn and Rosebud Counties, Montana: U.S. Geological Survey Bulletin 806-B, p. 15-67.

Cohen, A. C., 1959, Simplified estimators for the normal distribution when samples are singly censored or truncated: Technometrics, v. 1, no. 3, p. 217-237.

Connor, J. J., Keith, J. R., and Anderson, B. B., 1976, Trace-metal variation in soils and sagebrush in the Powder River basin, Wyoming and Montana: U.S. Geological Survey Journal of Research, v. 4, no. 1, p. 49-59.

Culbertson, W. C., 1980, Diagrams showing correlation of Paleocene coal beds underlying the Birney $1^{o}x1/2^{o}$ quadrangle, Big Horn, Rosebud, and Powder River Counties, Montana: U.S. Geological Survey Open-File Report 80-666, 2 sheets.

DeCarlo, J. A., Sheridan, E. T., and Murphy, Z. E., 1966, Sulfur content of United States coals: U.S. Bureau of Mines Information Circular 8312, 44 p.

Francis, Wilfried, 1961, Coal, its formation and composition: London, Edward Arnold (Publishers) Ltd., 806 p.

Hatch, J. R., and Swanson, V. E., 1977, Trace elements in Rocky Mountain coals, in Murray, D. K., ed., Geology of Rocky Mountain coal--A symposium: Colorado Geological Survey Resource Series 1, p. 143-165.

Lowry, H. H., ed., 1945, Chemistry of coal utilization, Volumes I and II: New York, John Wiley and Sons, Inc., 1868 p.

Lowry, H. H., 1963, Chemistry of coal utilization, supplementary volume: New York, John Wiley and Sons, Inc., 1142 p.

Matson, R. E., Blumer, J. W., and Wegelin, L. A., 1973, Quality and reserves of strippable coal, selected deposits, southeastern Montana: Montana Bureau of Mines and Geology Bulletin 91, 135 p.

Miesch, A. T., 1967, Methods of computation for estimating geochemical abundances: U.S. Geological Survey Professional Paper 574-B, 15 p.

Moore, E. S., 1940, Coal, its properties, analysis, classification, geology, extraction, uses and distribution: New York, John Wiley and Sons, Inc., 473 p.

Schopf, J. M., 1956, A definition of coal: Economic Geology, v. 51, no. 6, 54

521-527.

_____1960, Field description and sampling of coal beds: U.S. Geological Survey Bulletin 1111-B, 70 p.

_____1966, Definitions of peat and coal and of graphite that terminates the coal series (Graphocite): Journal of Geology, v. 74, no. 5, pt. 1, p. 584-592.

Snyder, N. H., 1950, Handbook on coal sampling: U.S. Bureau of Mines Technological Paper 133 (revised), 10 p.

Swanson, V. E. and Huffman, Claude, Jr., 1976, Guidelines for sample collecting and analytical methods used in the U.S. Geological Survey for determining chemical composition of coal: U.S. Geological Survey Circular 735, 11 p.

Swanson, V. E., Medlin, J. H., Hatch, J. R., Coleman, S. L., Wood, G. H., Jr., Woodruff, S. D., and Hildebrand, R. T., 1976, Collection, chemical analysis, and evaluations of coal samples in 1975: U.S. Geological Survey Open-File Report 76-468, 503 p.

Tomkeieff, S. I., 1954, Coals and bitumens and related fossil carbonaceous substances: London, Pergamon Press Ltd., 122 p.

U.S. Bureau of Mines, 1965, Bituminous coal, in Mineral facts and problems, 1965, p. 119-147.

U.S. Bureau of Mines and U.S. Geological Survey, 1976, Coal Resource Classification System of the U.S. Bureau of Mines and U.S. Geological Survey: U.S. Geological Survey Bulletin 1450-B, 7 p.

OPEN-FILE REPORT
81-1136
PLATE 1

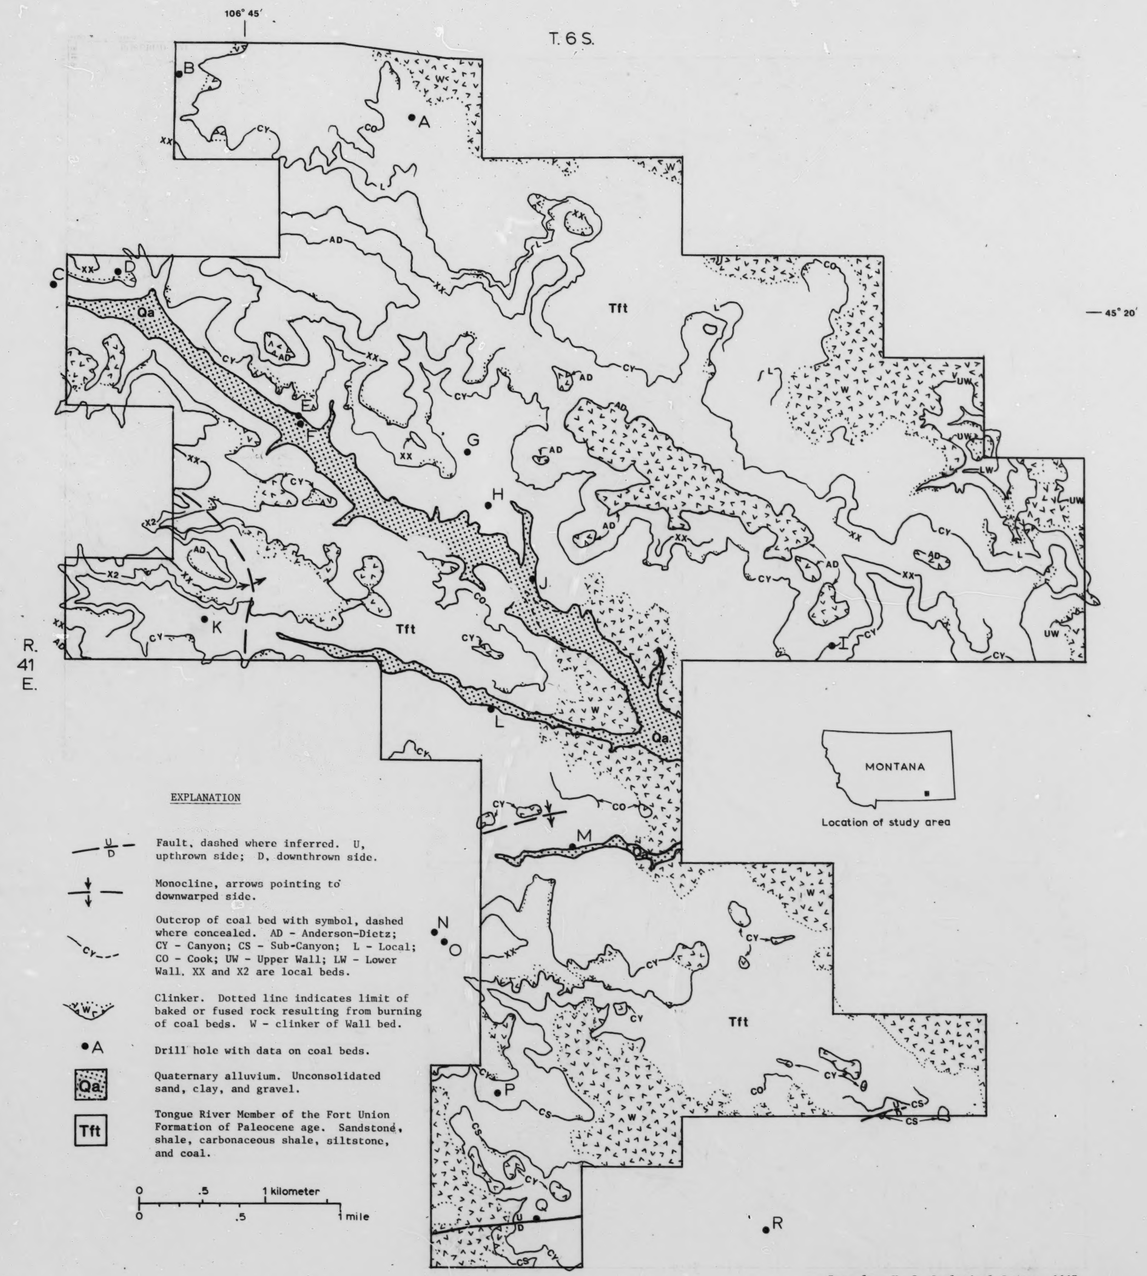
106° 45'
T. 6 S.
45° 20'
R. 41 E.
Qa
Tft
MONTANA
Location of study area
EXPLANATION
Fault, dashed where inferred. U, upthrown side; D, downthrown side.
Monocline, arrows pointing to downwarped side.
Outcrop of coal bed with symbol, dashed where concealed. AD - Anderson-Dietz; CY - Canyon; CS - Sub-Canyon; L - Local; CO - Cook; UW - Upper Wall; LW - Lower Wall. XX and X2 are local beds.
Clinker. Dotted line indicates limit of baked or fused rock resulting from burning of coal beds. W - clinker of Wall bed.
Drill hole with data on coal beds.
Quaternary alluvium. Unconsolidated sand, clay, and gravel.
Tongue River Member of the Fort Union Formation of Paleocene age. Sandstone, shale, carbonaceous shale, siltstone, and coal.
0 .5 1 kilometer
0 .5 1 mile

Base from U. S. Geological Survey, 1967
Geology mapped in 1978 and 1979 by S. A. Volz.

Plate 1 – Geologic map of the Prairie Dog Creek study area

By

Laura N. Robinson, William C. Culbertson, and Ronald H. Affolter

OPEN-FILE REPORT

81-1136

PLATE 2

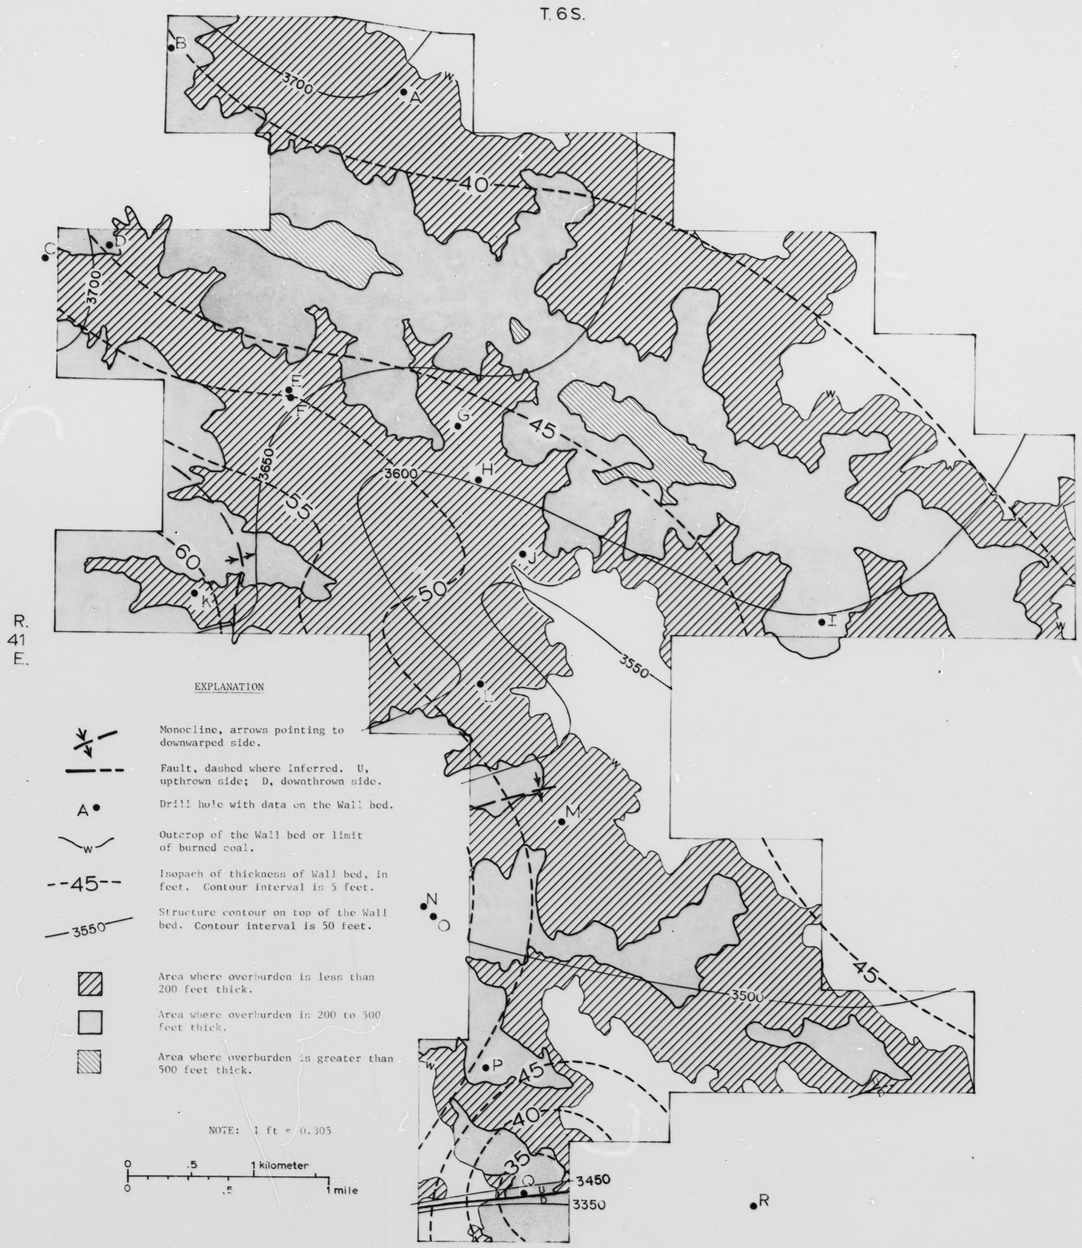

Plate 2 – Coal thickness, overburden thickness, and structure of the Wall coal bed in Prairie Dog Creek study area.

By

Laura N. Robinson, William C. Culbertson and Ronald H. Affolter

OPEN-FILE REPORT
81-1136
PLATE 3

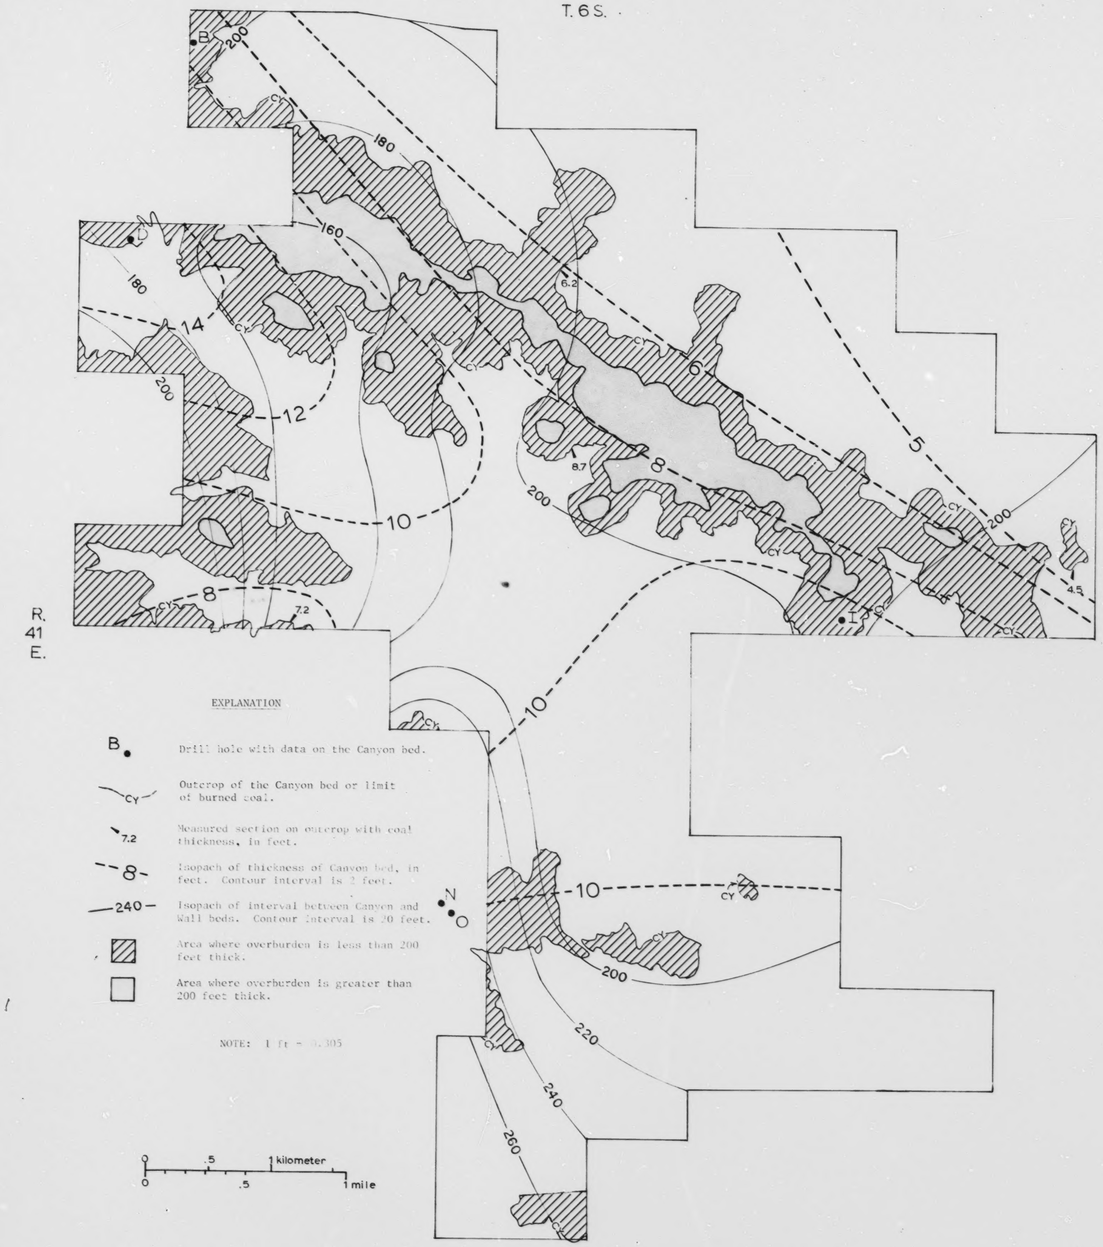

Plate 3 – Thickness of Canyon coal bed, thickness of overburden, and thickness of interval between Canyon and Wall beds in Prairie Dog Creek study area.

By
Laura N. Robinson, William C. Culbertson and Ronald H. Affolter

best copy available

OPEN-FILE REPORT

81-1136

PLATE 4

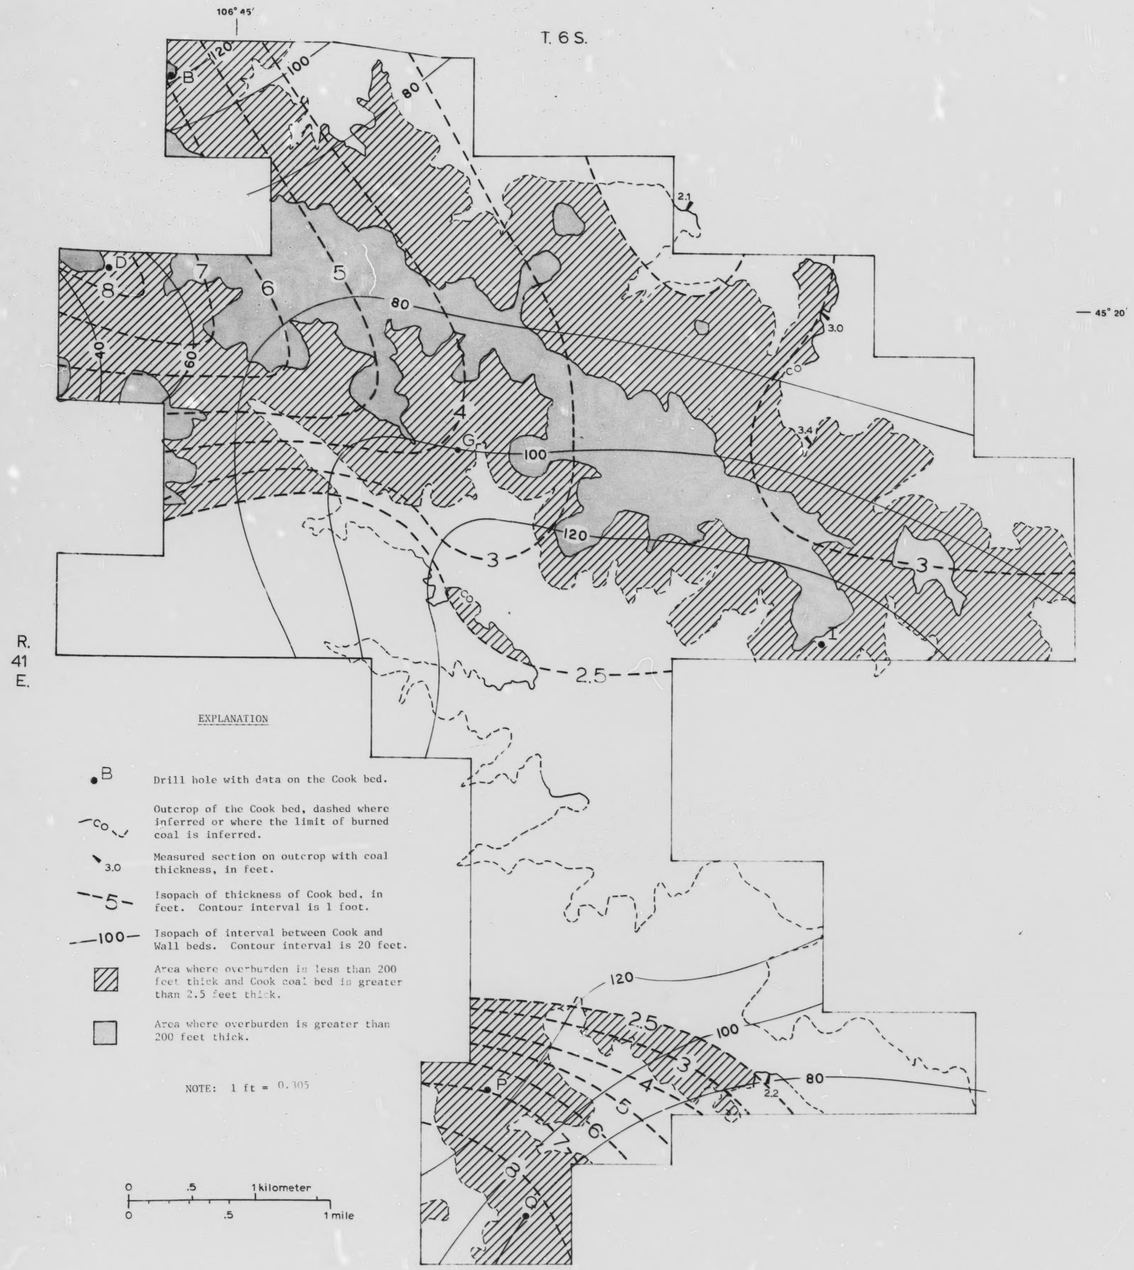
106° 45'
T. 6 S.
R. 41 E.
— 45° 20'
EXPLANATION
B
Drill hole with data on the Cook bed.
Outcrop of the Cook bed, dashed where inferred or where the limit of burned coal is inferred.
3.0
Measured section on outcrop with coal thickness, in feet.
5
Isopach of thickness of Cook bed, in feet. Contour interval is 1 foot.
100
Isopach of interval between Cook and Wall beds. Contour interval is 20 feet.
Area where overburden is less than 200 feet thick and Cook coal bed is greater than 2.5 feet thick.
Area where overburden is greater than 200 feet thick.
NOTE: 1 ft = 0.305
0 .5 1 kilometer
0 .5 1 mile

Plate 4 – Thickness of Cook coal bed, thickness of overburden, and thickness of interval between Cook and Wall beds in Prairie Dog Creek study area.

By

Laura N. Robinson, William C. Culbertson and Ronald H. Affolter